



GGB DP4/DP4B™

Maintenance-free



Designer's Handbook



Thyssing Industrial Supplies Pty Ltd

ABN 63 099 806 283

PO Box 3072, Ivanhoe North, Victoria 3079, Australia
136 – 138 Plenty Road, Preston, Victoria 3072, Australia
Ph: +61 3 9484 9550 Fax: +61 3 9484 9755

web: www.thyssing.com.au email: info@thyssing.com.au



GGB

BEARING TECHNOLOGY

an EnPro Industries company


GGB World Class

All the products described in this handbook are manufactured under DIN EN ISO 9001, ISO/TS 16949, OHSAS 18001 and ISO 14001 approved management systems.

All Certificates can be downloaded as PDF files from our website www.ggbearings.com.

In addition GGB North America has been certified AS9100 revision B complying with the requirements of aerospace industry's quality management system for the manufacture of metal-backed bearings and filament wound bearings and washers.

AMERICA

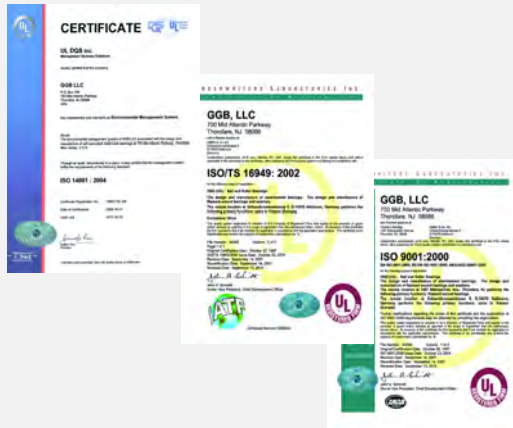

FRANCE



GERMANY



BRAZIL



SLOVAKIA



CHINA



Content

GGB World Class	2	5 Lubrication	23
1 Introduction	5	5.1 Lubricants	23
1.1 Characteristics and Advantages	5	5.2 Tribology	23
1.2 Applications	6	Hydrodynamic lubrication	23
2 Structure and Composition	7	Mixed film lubrication	24
2.1 Basic Forms	7	Boundary lubrication	24
Standard Components	7	5.3 Characteristics of Lubricated Bearings	24
Non-Standard Components	7	5.4 Design Guidance	25
3 Properties	8	5.5 Clearances for lubricated operation	26
3.1 Physical and Mechanical Properties	8	5.6 Grooving for lubricated operation	26
3.2 Chemical Properties	8	5.7 Mating Surface Finish for lubricated operation	26
3.3 Frictional Properties	9	5.8 Grease Lubrication	26
Effect of Temperature for unlubricated applications	9	6 Bearing Assembly	27
4 Bearing Performance	10	Dimensions and Tolerances	27
4.1 McPherson Strut Applications	10	6.1 Allowance for Thermal Expansion	27
Wear and Friction Properties	10	6.2 Tolerances for minimum clearance	28
McPherson Strut Test Rig	10	Burnishing	28
Cavitation Erosion Resistance	12	6.3 Counterface Design	29
Flow Erosion Resistance	13	6.4 Installation	30
4.2 Hydraulic Applications	14	Fitting of cylindrical Bushes	30
GGB Jupiter Test Rig	14	Fitting of flanged bushes	30
4.3 Dry Wear Performance	15	Insertion Forces	30
Design Factors	15	Alignment	31
Oscillating Movement	16	Sealing	31
Application Factors	17	6.5 Axial Location	31
Mating Surface	18	Fitting of Thrust Washers	31
Bore Burnishing	19	Slideways	32
Type of Load	19	7 Modification	33
4.4 Calculation of Bearing Service Life	20	7.1 Cutting and Machining	33
Specific load p	20	Drilling Oil Holes	33
High load factor a_E	20	Cutting Strip Material	33
Modified p_v Factor	20	7.2 Electroplating	33
Estimation of bearing life L_H	20	DP4 Components	33
Bore Burnishing	21		
Slideways	21		
4.5 Worked Examples	22		

8	Standard Products	34	9	Test Methods	48
8.1	DP4 Cylindrical bushes	34	9.1	Measurement of Wrapped Bushes	48
8.2	DP4 Flanged bushes	39		Test A of ISO 3547 Part 2	48
8.3	DP4 Flanged Washers	41		Test B (alternatively to Test A)	48
8.4	DP4 Thrust Washers	42		Test C	48
8.5	DP4B Cylindrical bushes	43		Measurement of Wall Thickness (alternatively to Test C)	48
8.6	DP4B Flanged bushes	45		Test D	48
8.7	DP4 Strip	47	10	Data Sheet for bearing design	49
8.8	DP4B Strip	47		Formula Symbols and Designations	50

1 Introduction

The purpose of this handbook is to provide comprehensive technical information on the characteristics of DP4™ and DP4B™ bearings.

The information given permits designers to establish the correct size of bearing required and the expected life and performance.

In addition, your local sales representative is available to assist you with your design.

Complete information on the range of DP4 standard stock products is given together with details of other DP4 products.

GGB is continually refining and extending its experimental and theoretical knowledge and, therefore, when using this brochure it is always worth-while to contact GGB should additional information be required.

As it is impossible to cover all conditions of operation which arise in practice, customers are advised to carry out prototype testing wherever possible.

1.1 Characteristics and Advantages

The DP4 and DP4B materials offer the following characteristics:

- Good frictional properties with negligible stick-slip
- High static and dynamic load capacity
- Suitable for rotating, oscillating, reciprocating and sliding movements
- Compact size and low weight
- Prefinished that requires no machining after assembly
- Possibility to burnish for reduced operating clearance
- No water absorption and therefore dimensionally stable
- Suitable for a wide operating temperature range from -200 to +280 °C
- DP4B with bronze backing for increased corrosion resistance
- **Lead free in compliance with European RoHS 2011/96/EC, directives (see page 51)**

In particular, depending on the dry running conditions, DP4 and DP4B materials

present the following performance advantages:

Dry conditions

- Good friction and wear performance under light duty conditions
- Particularly suitable for intermittent oscillating and reciprocating movements
- Maintenance free as no external lubrication required
- Seizure resistant.

Lubricated conditions

- Good wear and friction performance over a wide range of load, speed and temperature conditions
- High wear resistance in boundary operating conditions
- High resistance of bearing surface under fluid cavitation and flow erosion conditions
- Suitable for operation in diverse fluids (oil, fuel, solvents, refrigerants, water).

1.2 Applications

Given the performance characteristics in both dry and lubricated operating conditions, DP4 and DP4B bearing

materials are extensively used in a wide range of automotive and industrial applications, such as:

Automotive

Braking systems, clutches, gearbox and transmissions, hinges - door bonnet and boot, convertible roof tops, pedal systems, pumps - axial, radial, gear and vane, seat mechanisms, steering systems, struts and shock absorbers, wiper systems.

Industrial

Aerospace, agricultural, construction equipment, food and beverage, marine, material handling, office equipment, packaging equipment, pneumatic and hydraulic cylinders, railroad and tramways, textile machinery, valves.

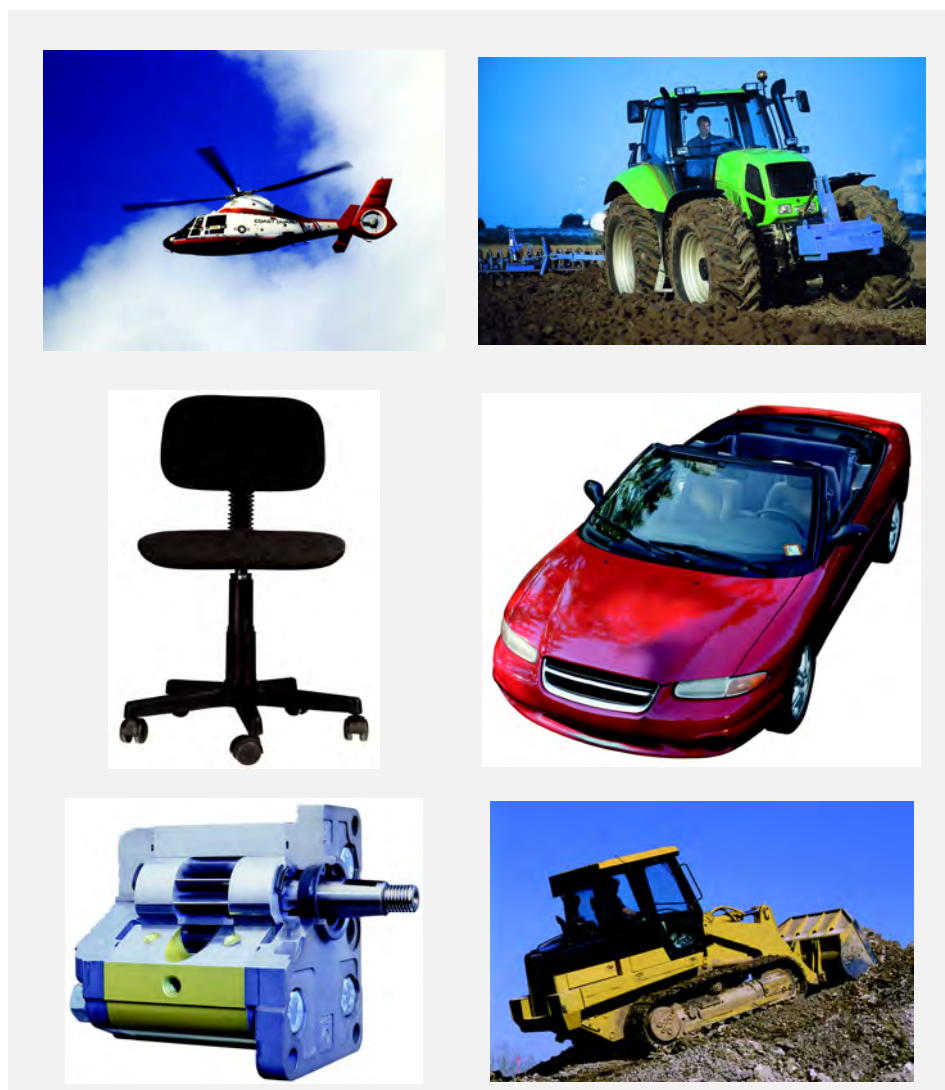


Fig. 1: Applications for DP4 and DP4B

2 Structure and Composition

DP4 is a composite bearing material. It consists of a steel DP4/bronze DP4B backing to which is bonded a porous sinter bronze interlayer which is overlaid and impregnated with Polytetrafluoroethylene (PTFE) containing a mixture of inorganic

fillers and special polymer fibres. The steel DP4/bronze DP4B backing provides mechanical strength and the bronze sinter layer provides a strong mechanical bond for the filled bearing lining.

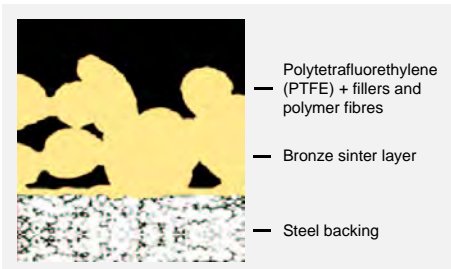


Fig. 2: DP4-microsection

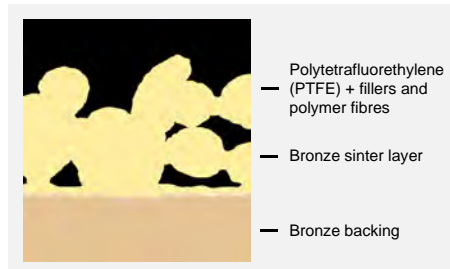


Fig. 3: DP4B-microsection

2.1 Basic Forms

Standard Components

These products are manufactured to International, National or GGB standards. The following components are standard stock products:

- Cylindrical Bushes
- Flanged Bushes
- Thrust Washers
- Flanged Washers
- Strip Material

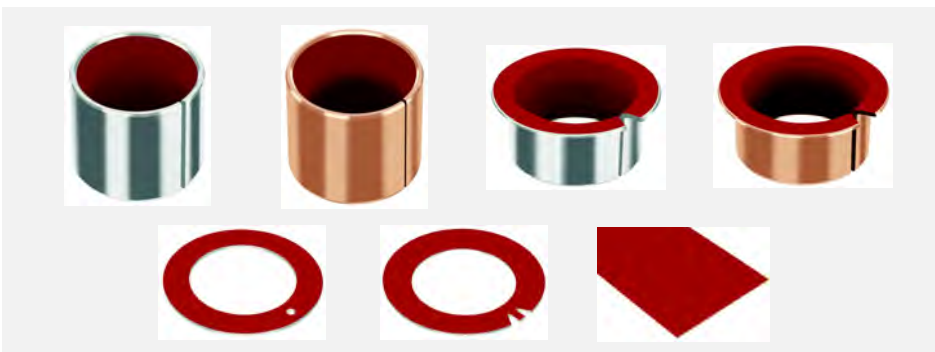


Fig. 4: Standard stock products

Non-Standard Components

These products are manufactured to customer's requirements and include for example:

- Modified Standard Components
- Half Bearings
- Flat Components
- Deep Drawn Parts
- Pressings
- Stampings

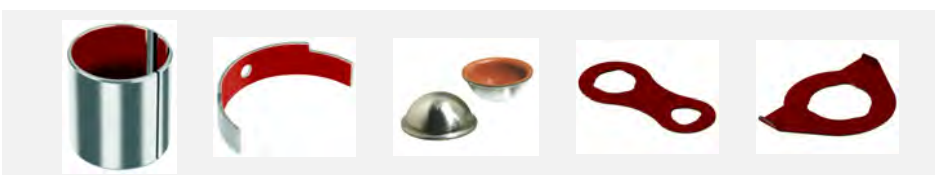


Fig. 5: Non-Standard Components

3 Properties

3.1 Physical and Mechanical Properties

	Symbol	Value		Unit	Comment	
		DP4	DP4B			
Physical Properties	Coefficient of linear thermal expansion:					
	Parallel to surface	α_1	11	18	$10^{-6}/K$	
	Normal to surface	α_2	30	36	$10^{-6}/K$	
	Maximum Operating Temperature	T_{max}	+280	+280	°C	
Mechanical Properties	Minimum Operating Temperature	T_{min}	-200	-200	°C	
	Compressive Yield Strength	σ_c	350	300	MPa	measured on disc 5 mm diameter x 2.45 mm thick.
	Maximum Load					
	Static	$P_{sta,max}$	250	140	MPa	
	Dynamic	$P_{dyn,max}$	140	140	MPa	

Table 1: Physical and mechanical properties of DP4 and DP4B

3.2 Chemical Properties

The following table provides an indication of the chemical resistance of DP4 to various chemical media. It is recommended, that the chemical resistance is confirmed by testing.

+	Satisfactory: Corrosion damage is unlikely to occur.
o	Acceptable: Some corrosion damage may occur but this will not be sufficient to impair either the structural integrity or the tribological performance of the material.
-	Unsatisfactory: Corrosion damage will occur and is likely to affect either the structural integrity and/or the tribological performance of the material.

	Chemical	%	°C	Rating	
				DP4	DP4B
Strong Acids	Hydrochloric Acid	5	20	-	-
	Nitric Acid	5	20	-	-
	Sulphuric Acid	5	20	-	-
Weak Acids	Acetic Acid	5	20	-	o
	Formic Acid	5	20	-	o
Bases	Ammonia	10	20	o	-
	Sodium Hydroxide	5	20	o	o
Solvents	Acetone		20	+	+
	Carbon Tetrachloride		20	+	+
Lubricants and fuels	Paraffin		20	+	+
	Gasolene		20	+	+
	Kerosene		20	+	+
	Diesel Fuel		20	+	+
	Mineral Oil		70	+	+
	HFA-ISO46 High Water Fluid		70	+	+
	HFC-Water-Glycol		70	+	+
	HFD-Phosphate Ester		70	+	+
	Water		20	o	+
Sea Water		20	-	o	

Table 2: Chemical resistance of DP4 and DP4B

3.3 Frictional Properties

DP4 bearings show negligible 'stick-slip' and provide smooth sliding between adjacent surfaces. The coefficient of friction of DP4 depends upon:

- The specific load p [MPa]
- The sliding speed v [m/s]
- The roughness of the mating running surface R_a [μm]
- The bearing temperature T [$^{\circ}\text{C}$].

A typical relationship is shown in Fig. 6, which can be used as a guide to establish

the actual friction under clean, dry conditions after running in.

Exact values may vary by $\pm 20\%$ depending on operating conditions. Before running in, the friction may be up to 50% higher.

After progressively longer periods of dwell under load (e.g. hours or days) the static coefficient of friction on the first movement may be between 1.5 and 3 times greater, particularly before running in.

Effect of Temperature for unlubricated applications

The coefficient of friction of DP4 varies with temperature. Typical values are shown in Fig. 7 for temperatures up to 250 $^{\circ}\text{C}$. Friction increases at bearing temperatures below 0 $^{\circ}\text{C}$.

Where frictional characteristics are critical to a design they should be established by prototype testing.

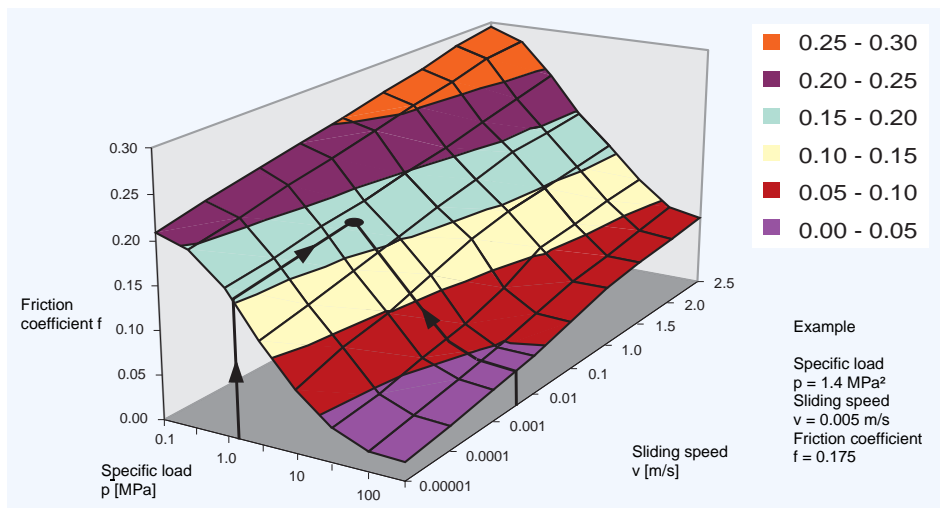


Fig. 6: Variation of friction coefficient f with specific load p and speed v at temperature $T = 25 \text{ }^{\circ}\text{C}$

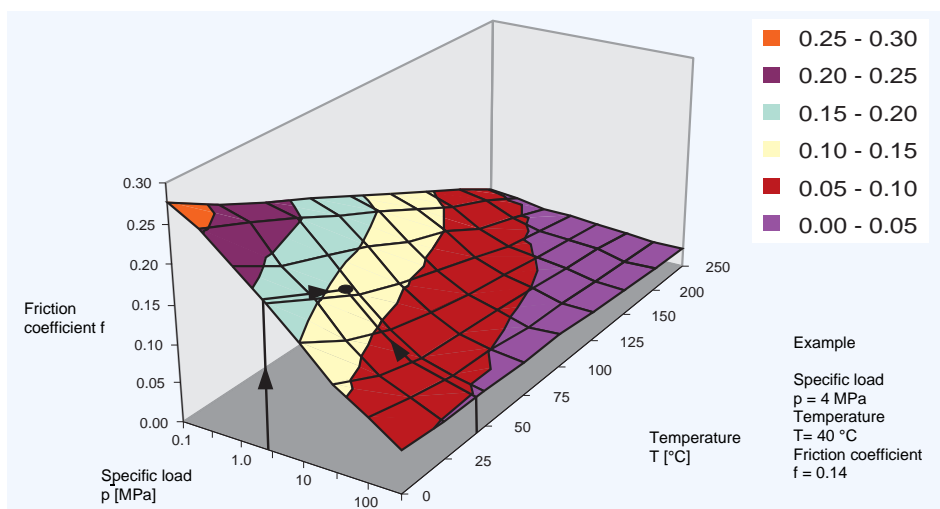


Fig. 7: Variation of friction coefficient f with specific load p and temperature T at speed $v = 0.01 \text{ m/s}$

4 Bearing Performance

4.1 McPherson Strut Applications

DP4 has been developed to provide improved wear, erosion resistance and reduced friction in McPherson strut piston rod guide bush applications under the most demanding of operating conditions.

In the following sections, the performance of DP4 is compared with that of the material used in the majority of this type of application.

Wear and Friction Properties

The wear and frictional performance of DP4 has been evaluated in the piston rod guide bush application of a McPherson strut shock absorber using the test rig shown in Fig. 8. The test conditions are

designed to simulate the operational duty of the test strut in service and differ in detail according to the strut manufacturer. The test conditions used are given in Table 3 and Table 4.

McPherson Strut Test Rig

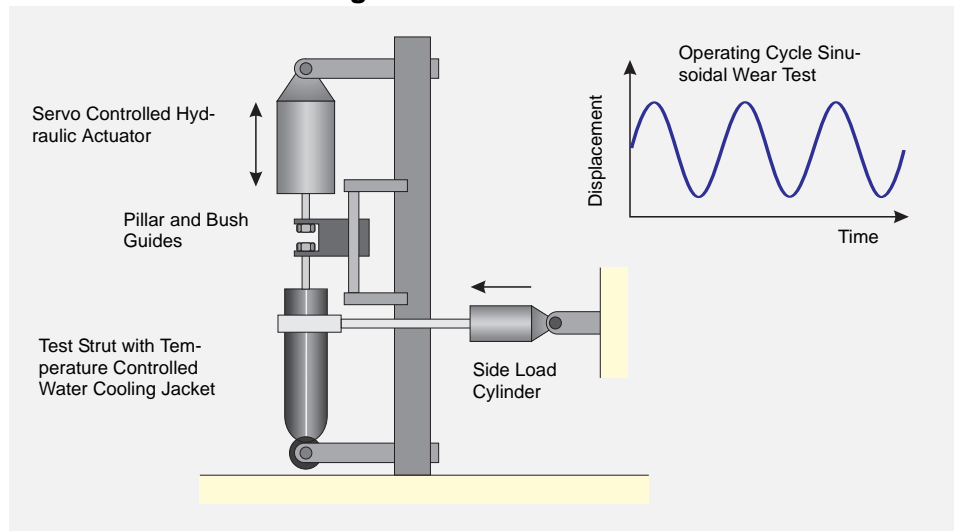


Fig. 8: Principle of the Strut Test Rig

Strut Wear - Test conditions

Waveform	Sine
Frequency	2.5 Hz
Side Load	890 N
Test Duration	100 hours
Stroke	100 mm
Mean Diametral Clearance	0.06 mm
Lubricant	TEX 0358
Foot Valve Temperature	70 °C

Table 3: McPherson strut wear test conditions

Strut Friction - Test conditions

Waveform	Sine
Frequency	0.1 Hz
Side Load	600 N
Stroke	70 mm
Mean Diametral Clearance	0.06 mm
Lubricant	TEX 0358
Foot Valve Temperature	Ambient

Table 4: McPherson strut friction test conditions

The relative wear and frictional performance of DP4 tested under these conditions are shown in Figures 9-11. Actual results for the wear rate and friction are not quoted because these depend

strongly on the actual test conditions and design of the strut under test. The relative performance plots shown thus provide the best indication as to the benefits offered by DP4 in this class of application.

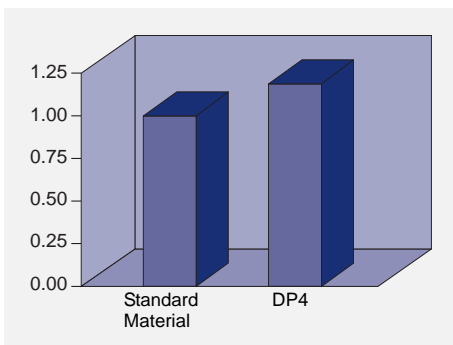


Fig. 9: Relative wear resistance

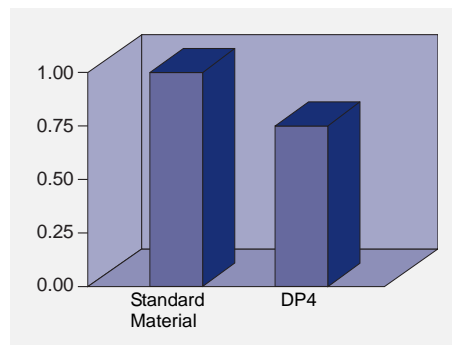


Fig. 10: Relative static friction coefficient

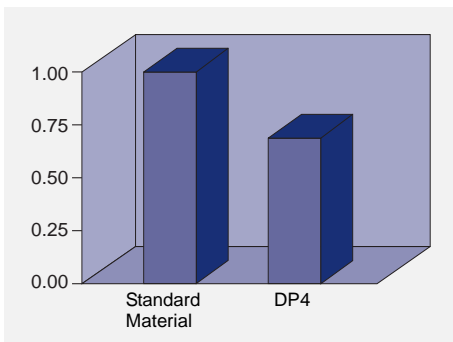


Fig. 11: Relative dynamic friction coefficient

Cavitation Erosion Resistance

Under certain operating conditions, the PTFE lining of the McPherson strut piston rod guide bush can suffer erosion damage, due to cavitation and flow erosion effects from the oil film within the bearing. The test

rig shown in Fig. 12 is designed to reproduce the cavitation erosion damage to the bearing lining of the test specimen. The test conditions are given in Table 5.

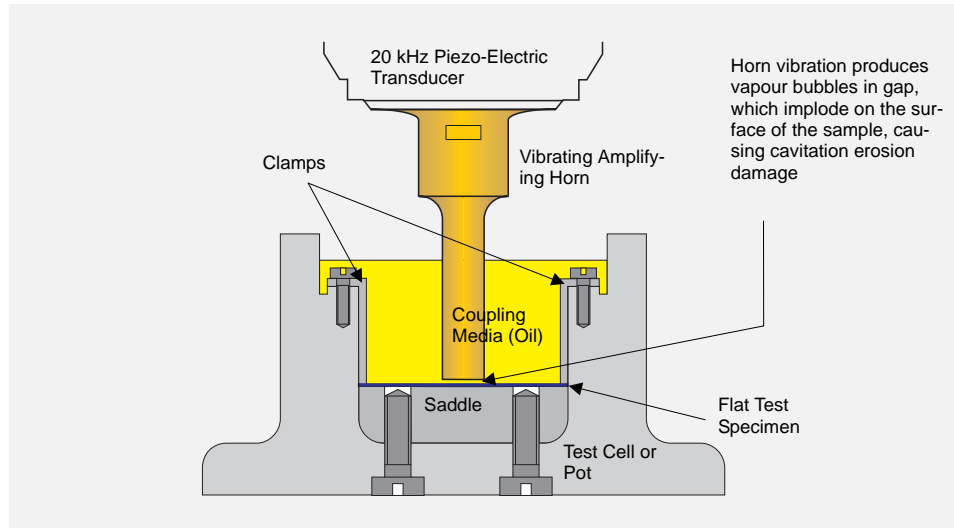


Fig. 12: Principle of the cavitation erosion test rig

Cavitation Erosion - Test Conditions

Amplitude	0.015 mm
Frequency	20 kHz
Separation	1 mm
Test Duration	30 minutes
Lubricant	TEX 0358
Temperature	Ambient

Table 5: Cavitation erosion test conditions

The relative resistance to cavitation damage of DP4 as evaluated on this test rig is shown in Fig. 13.

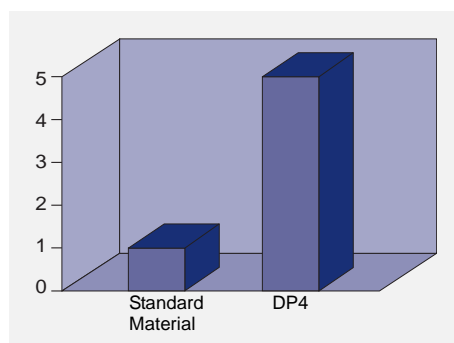


Fig. 13: Relative resistance to cavitation erosion

Flow Erosion Resistance

The test rig shown in Fig. 14 is designed to reproduce flow erosion damage to the bearing lining of the test specimen. The test conditions are given in Table 6.

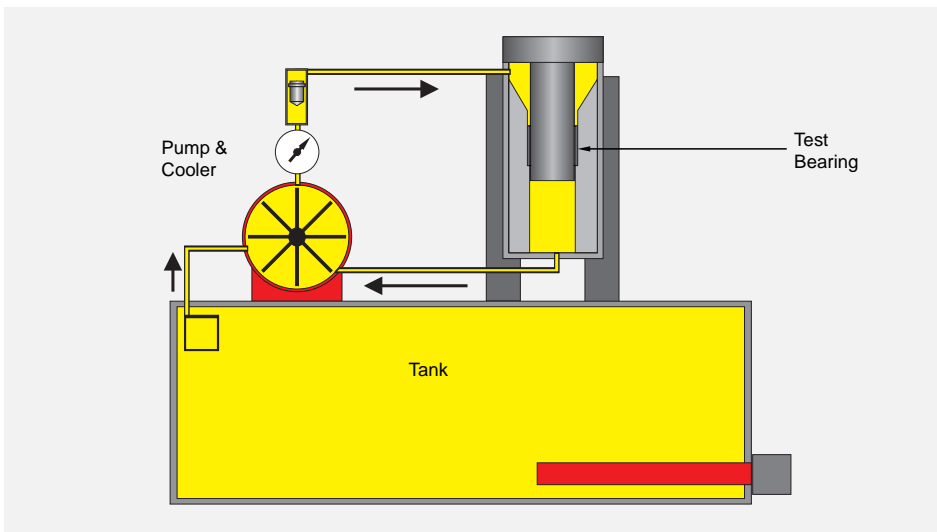


Fig. 14: Principle of the flow erosion test rig

Flow Erosion - Test Conditions

Bearing Diameter	20 mm
Bearing Length	15 mm
Diametral Clearance	0.11 mm
Pressure	13.8 MPa
Flow Rate	5 l/min
Test Duration	20 hours
Shaft Surface Finish	0.15 $\mu\text{m} \pm 0.05$
Temperature	Ambient

Table 6: Flow erosion test conditions

The relative resistance to flow erosion damage of DP4 as evaluated on this test rig is shown in Fig. 15.

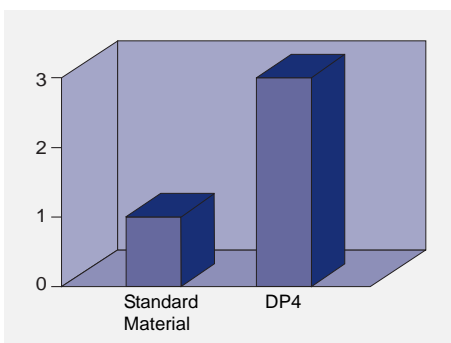


Fig. 15: Relative resistance to flow erosion

4.2 Hydraulic Applications

DP4 also shows excellent wear and frictional performance in a wide range of oil lubricated hydraulic applications.

The wear resistance of DP4 under steady load oil immersed boundary lubrication

conditions has been evaluated using the test rig shown in Fig. 16. The test conditions are given in Table 7.

GGB Jupiter Test Rig

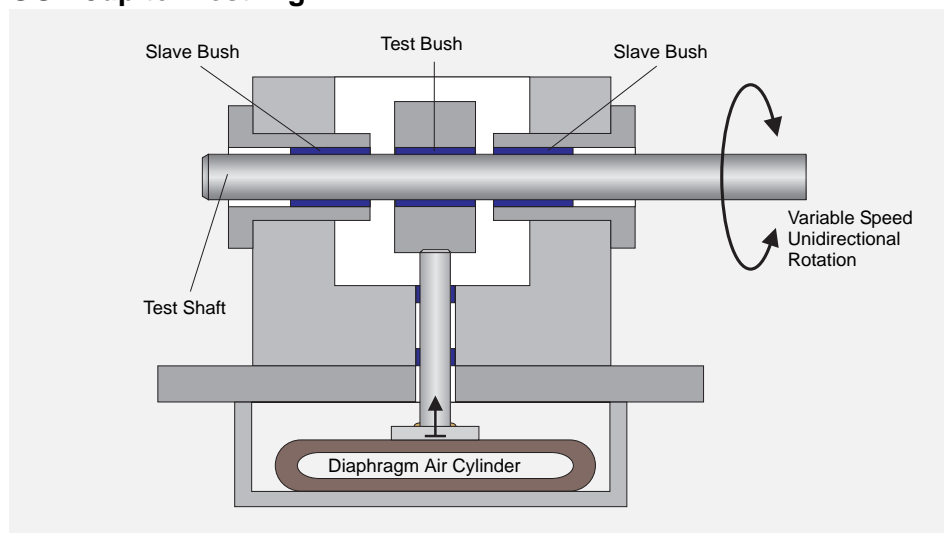


Fig. 16: Principle of the GGB Jupiter test rig

Lubricated Wear - Test Conditions

Bearing Diameter	20 mm
Bearing Length	15 mm
Mean Diametral Clearance	0.10 mm
Speed	0.11 m/s
Lubricant	ISO VG 46 hydraulic oil

Table 7: Lubricated wear test conditions

The relative pv limits with boundary lubrication of DP4 and the material used in many high performance hydraulic pump applications as determined from these

tests are shown in Fig. 17. The limiting pv depends upon the actual operating conditions and hence the relative performance only is given for guidance.

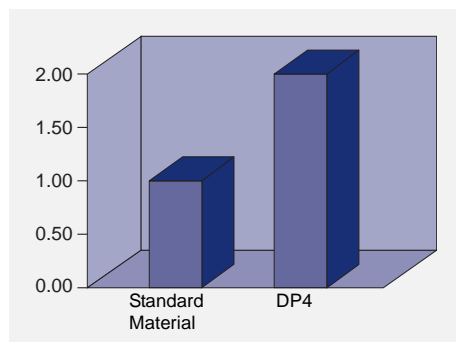


Fig. 17: Relative pv limits

4.3 Dry Wear Performance

Design Factors

The main parameters when determining the size or calculating the service life for a DP4 bearing are:

- Specific Load Limit p_{lim}
- pv Factor
- Mating surface roughness R_a

- Mating surface material
- Temperature T
- Other environmental factors e.g. housing design, dirt, lubrication

The following calculation can be used to estimate the bearing service life of DP4 under dry running conditions.

Specific Load p

For the purpose of assessing bearing performance the specific load p is defined as the working load divided by the projected area of the bearing and is expressed in MPa.

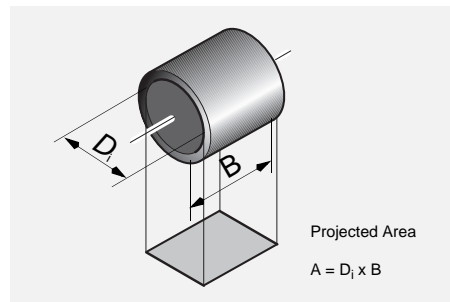


Fig. 18: Projected Area

Cylindrical Bush

$$(4.3.1) \quad p = \frac{F}{D_i \cdot B} \quad [\text{MPa}]$$

Flanged Bush (Axial Loading)

$$(4.3.3) \quad p = \frac{F}{0.04 \cdot (D_{fi}^2 - D_i^2)} \quad [\text{MPa}]$$

Thrust Washer

$$(4.3.2) \quad p = \frac{4F}{\pi \cdot (D_o^2 - D_i^2)} \quad [\text{MPa}]$$

Slideway

$$(4.3.4) \quad p = \frac{F}{L \cdot W} \quad [\text{MPa}]$$

Specific Load Limit p_{lim}

The maximum load which can be applied to a DP4 bearing can be expressed in terms of the Specific Load Limit, which depends on the type of the loading. It is highest under steady loads. Conditions of dynamic load or oscillating movement which produce fatigue stress in the bearing result in a reduction in the permissible Specific Load Limit.

In general the specific load on a DP4 bearing should not exceed the Specific Load Limits given in Table 8.

The values of Specific Load Limit specified in Table 8 assume good alignment between the bearing and mating surface (Fig. 35).

Maximum specific load p_{lim}

Type of loading	p_{lim} [MPa]									
steady load, rotating movement	140									
steady load, oscillating movement										
p_{lim}	140	140	115	95	85	80	60	44	30	20
No. of movement cycles Q	1000	2000	4000	6000	8000	10^4	10^5	10^6	10^7	10^8
dynamic load, rotating or oscillating movement										
p_{lim}	60	60	50	46	42	40	30	22	15	10
No. of load cycles Q	1000	2000	4000	6000	8000	10^4	10^5	10^6	10^7	10^8

Table 8: Specific load limit

Permanent deformation of the DP4 bearing lining may occur for specific loads above 140 MPa unless with slow intermittent movements. Under these conditions, it is recommended to contact GGB for further information.

The permissible maximum load on a thrust washer is higher than that on the flange of a flanged bush, and under conditions of high axial loads a thrust washer should be specified.

Sliding Speed v

Speeds in excess of 2.5 m/s sometimes lead to overheating, and a running in procedure may be beneficial.

This could consist of a series of short runs progressively increasing in duration from an initial run of a few seconds.

Calculation of Sliding Speed v

Continuous Rotation

Cylindrical Bush

$$(4.3.5) \quad v = \frac{D_i \cdot \pi \cdot n}{60 \cdot 10^3} \quad [\text{m/s}]$$

$$v = \frac{D_i \cdot \pi \cdot n}{60 \cdot 10^3}$$

Thrust Washer

$$(4.3.6) \quad v = \frac{D_o + D_i}{2} \cdot \pi \cdot n \quad [\text{m/s}]$$

$$v = \frac{D_o + D_i}{2} \cdot \pi \cdot n$$

Oscillating Movement

Cylindrical Bush

$$(4.3.7) \quad v = \frac{D_i \cdot \pi}{60 \cdot 10^3} \cdot \frac{4\phi \cdot n_{osc}}{360} \quad [\text{m/s}]$$

$$v = \frac{D_i \cdot \pi}{60 \cdot 10^3} \cdot \frac{4\phi \cdot n_{osc}}{360}$$

Thrust Washer

$$(4.3.8) \quad v = \frac{D_o + D_i}{2} \cdot \pi \cdot \frac{4\phi \cdot n_{osc}}{360} \quad [\text{m/s}]$$

$$v = \frac{D_o + D_i}{2} \cdot \pi \cdot \frac{4\phi \cdot n_{osc}}{360}$$

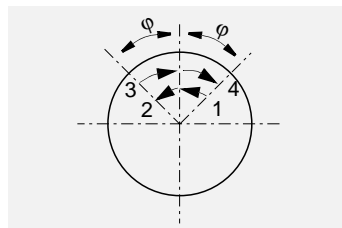


Fig. 19: Oscillating movement

pv Factor

The useful operating life of a DP4 bearing is governed by the pv factor, the product of the specific load p [MPa] and the sliding speed v [m/s].

For thrust washers and flanged bush thrust faces the rubbing velocity at the mean diameter is used.

	DP4	Unit
p	140	MPa
v	2.5	m/s
pv continuous	0.5	MPa x m/s
pv intermittent	1.0	MPa x m/s

Table 9: Typical data p , v , pv

pv factors up to 1.0 Mpa x m/s can be accommodated for short periods, whilst for continuous rating, pv factors up to 0.5 MPa x m/s can be used, depending upon the operating life required.

Calculation of pv Factor

$$(4.3.9) \quad [MPa \times m/s]$$

$$pv = p \cdot v$$

Application Factors

The following factors influence the bearing performance of DP4 and must be considered in calculating the required

dimensions or estimating the bearing life for a particular application.

Temperature

The useful life of a DP4 bearing depends upon the operating temperature.

Under dry running conditions frictional heat is generated at the rubbing surface of the bearing dependent on the pv condition. For a given pv factor the operating temperature of the bearing depends upon the temperature of the surrounding environment, the heat dissipation

properties of the housing and the mating surface. Intermittent operation affects the heat dissipation from the assembly and hence the operating temperature of the bearing.

The effect of temperature on the operating life of DP4 bearings is indicated by the factor a_T shown in Table 10.

Mode of Operation	Nature of housing	Temperature of bearing environment T_{amb} [°C] and Temperature application factor a_T					
		25	60	100	150	200	280
Dry continuous operation	Average heat dissipating qualities	1.0	0.8	0.6	0.4	0.2	0.1
Dry continuous operation	Light pressings or isolated housing with poor heat dissipating qualities	0.5	0.4	0.3	0.2	0.1	-
Dry continuous operation	Non-metallic housings with bad heat dissipating qualities	0.3	0.3	0.2	0.1	-	-
Dry intermittent operation (duration less than 2 min, followed by a longer dwell period)	Average heat dissipating qualities	2.0	1.6	1.2	0.8	0.4	0.2

Table 10: Temperature application factor a_T

Mating Surface

The effect of mating surface material type on the operating life of DP4 bearings is indicated by the mating surface factor a_M and life correction constant a_L shown in Table 11.

Note:

The factor values given assume a mating surface finish of $R_a = 0.4 \pm 0.1 \mu\text{m}$.

- A ground surface is preferred to fine turned.
- Surfaces should be cleaned of abrasive particles after polishing.
- Cast iron surfaces should be ground to $R_a = 0.3 \pm 0.1 \mu\text{m}$.
- The grinding cut should be in the same direction as the bearing motion relative to the shaft.

Material	Mating Surface Factor a_M	Life correction constant a_L
Steel and Cast Iron		
Carbon Steel	1	400
Carbon Manganese Steel	1	400
Alloy Steel	1	400
Case Hardened Steel	1	400
Nitrided Steel	1	400
Salt bath nitrocarburised	1	400
Stainless Steel (7-10 % Ni, 17-20 % Cr)	2	400
Cast Iron ($0.3 \pm 0.1 \mu\text{m } R_a$)	1	400

Table 11: Mating surface factor a_M and life correction constant a_L

Bearing Size

The running clearance of a DP4 bearing increases with bearing diameter resulting in a proportionally smaller contact area between the shaft and bearing. This reduction in contact area has the effect of

increasing the actual unit load and hence p_v factor. The bearing size factor (Fig. 21) is used in the design calculations to allow for this effect.

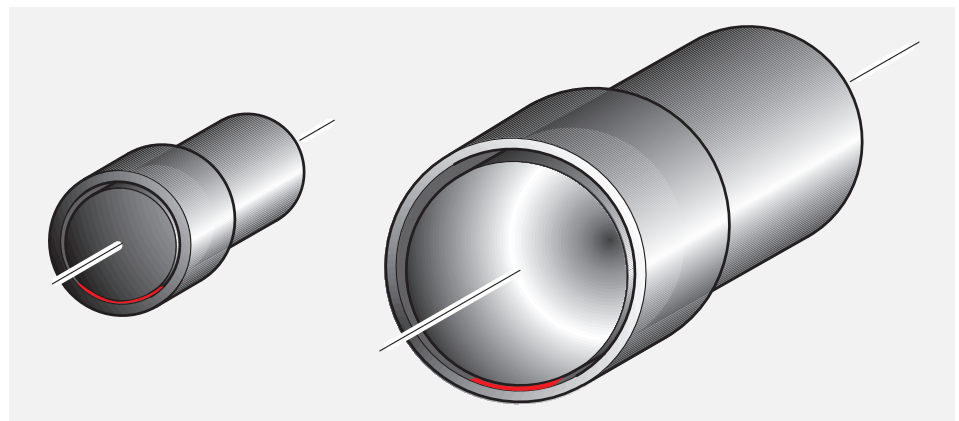


Fig. 20: Contact area between bearing and shaft

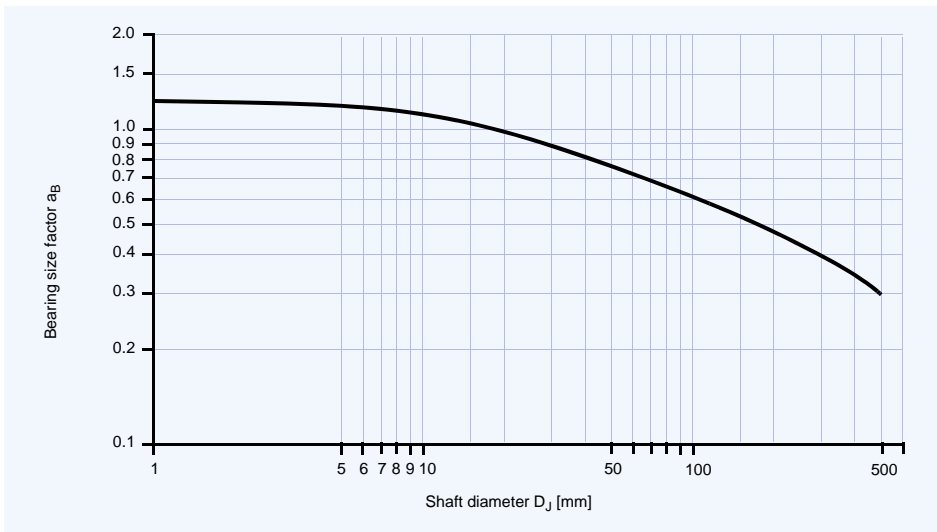


Fig. 21: Bearing size factor a_B

Bore Burnishing

Burnishing the bore of a DP4 bearing given in Table 12 is used in the design results in a reduction in the wear performance. The application factor a_C Machining DP4 is not recommended.

Degree of sizing	Application factor a_C	
Burnishing: Excess of burnishing tool diameter over mean bore size	0.025 mm	0.8
	0.038 mm	0.6
	0.050 mm	0.3

Table 12: Bore burnishing application factor a_C

Type of Load

The type of load is considered in formula (4.4.9), Page 20 and (4.4.10), Page 20.

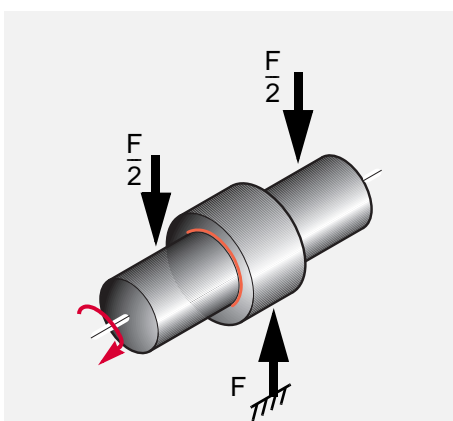


Fig. 22: Steady load, bush stationary, shaft rotating

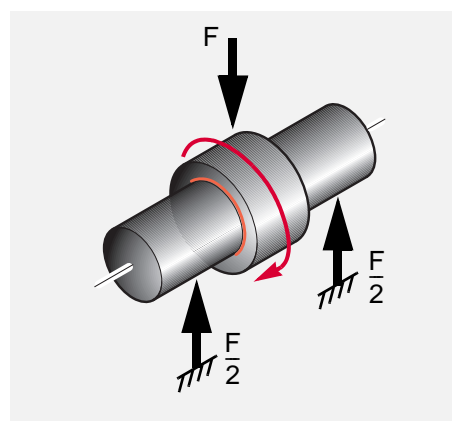


Fig. 23: Rotating load, shaft stationary, bush rotating

4.4 Calculation of Bearing Service Life

Where the size of a bearing is governed largely by the space available the following calculation can be used to determine

whether its useful life will satisfy the requirements. If the calculated life is inadequate, a redesign should be considered.

Specific load p

Bushes

(4.4.1) [MPa]

$$p = \frac{F}{D_i \cdot B}$$

Thrust Washers

(4.4.3) [MPa]

$$p = \frac{4F}{\pi \cdot (D_o^2 - D_i^2)}$$

Flanged Bushes

(4.4.2) [MPa]

$$p = \frac{F}{0.04 \cdot (D_{fl}^2 - D_i^2)}$$

High load factor a_E

If a_E is negative then the bearing is overloaded. Increase the bearing diameter and/or length.

(4.4.4) [-]

$$a_E = \frac{p_{lim} - p}{p_{lim}}$$

p_{lim} see Tab. 8, page 14

Modified p_v Factor

Bushes

(4.4.5) [MPa x m/s]

$$p_v = \frac{5.25 \cdot 10^{-5} F \cdot n}{a_E \cdot B \cdot a_T \cdot a_M \cdot a_B}$$

Flanged Bushes

(4.4.6) [MPa x m/s]

$$p_v = \frac{6.5 \cdot 10^{-4} F \cdot n}{a_E \cdot (D_{fl} - D_i) \cdot a_T \cdot a_M \cdot a_B}$$

Thrust Washers

(4.4.7) [MPa x m/s]

$$p_v = \frac{3.34 \cdot 10^{-5} F \cdot n}{a_E \cdot (D_o - D_i) \cdot a_T \cdot a_M \cdot a_B}$$

For oscillating movement, calculate the average rotational speed.

(4.4.8) [1/min]

$$n = \frac{4\phi \cdot n_{osc}}{360}$$

Estimation of bearing life L_H

Bushes (Steady load)

(4.4.9) [h]

$$L_H = \frac{265}{p_v} - a_L$$

Bushes (Rotating load)

(4.4.10) [h]

$$L_H = \frac{530}{p_v} - a_L$$

Flanged Bushes (Axial load)

(4.4.11) [h]

$$L_H = \frac{175}{pv} - a_L$$

a_L see Table 11, Page 18

Thrust Washers

(4.4.12) [h]

$$L_H = \frac{175}{pv} - a_L$$

Bore Burnishing

If the DP4 bush is bore burnished then this must be allowed for in estimating the bearing life by the application factor a_C (Table 12, Page 19).

Estimated Bearing Life

(4.4.13) [h]

$$L_H = L_H \cdot a_C$$

a_C see Table 12, Page 19

For Oscillating Movements or Dynamic loads

Calculate estimated number of cycles Z_T

(4.4.14) [cycles]

$$Z_T = L_H \cdot n_{osc} \cdot 60$$

If the required bearing life is known, the total number of cycles can be determined.

Check that Z_T is less than total number of cycles Q for the operating specific load p_{lim} (Table 8, Page 16).

If Z_T < Q, bearing life will be limited by wear after Z_T cycles.

If Z_T > Q, bearing life will be limited by fatigue after Z_T cycles.

(4.4.15) [cycles]

$$Z_T = L_H \cdot C \cdot 60$$

Slideways

Specific load factor

(4.4.16) [-]

$$a_{E1} = A - \frac{F}{p_{lim}}$$

If negative the bearing is overloaded and the bearing area should be increased.

Speed, temperature and material application factor

(4.4.17) [-]

$$a_{E2} = \frac{280 \cdot a_T \cdot a_M}{F \cdot v}$$

a_T see Table 10, Page 17
a_M see Table 11, Page 18

Relative contact area factor

(4.4.18) [-]

$$a_{E3} = \frac{A}{A_M}$$

Estimated bearing life

(4.4.19) [-]

$$L_H = a_{E1} \cdot a_{E2} \cdot a_{E3} - a_L$$

Note:

Estimated bearing lives greater than 4000 hours are subject to error due to inaccuracies in the extrapolation of test data.

4.5 Worked Examples

Cylindrical Bush

Given:			
Load Details	Steady Load	Inside Diameter D_i	40 mm
	Continuous Rotation	Length B	30 mm
Shaft	Steel	Bearing Load F	5000 N
	Unlubricated at 25 °C	Rotational Speed N	25 1/min

Calculation Constants and Application Factors			
Specific Load Limit p_{lim}	140 MPa	(Table 8, Page 16)	
Application Factor a_T	1.0	(Table 10, Page 17)	
Material Application Factor a_M	1.0	(Table 11, Page 18)	
Bearing Size Factor a_B	0.85	(Fig. 21, Page 19)	
Life Correction Constant a_L	400	(Table 11, Page 18)	

Calculation	Ref	Value
Specific Load p [MPa]	(4.4.1), Page 20	$p = \frac{F}{D_i \cdot B} = \frac{5000}{40 \cdot 30} = 4.17$
Sliding Speed v [m/s]	(4.3.5), Page 16	$v = \frac{D_i \cdot \pi \cdot n}{60 \cdot 10^3} = \frac{40 \cdot 3.14 \cdot 25}{60 \cdot 10^3} = 0.052$
High Load Factor a_E [-] (must be >0)	(4.4.4), Page 20	$a_E = \frac{p_{lim} - p}{p_{lim}} = \frac{140 - 4.17}{140} = 0.97$
Modified pv Factor [MPa x m/s]	(4.4.5), Page 20	$pv = \frac{5.25 \cdot 10^{-5} \cdot F \cdot n}{a_E \cdot B \cdot a_T \cdot a_M \cdot a_B} = \frac{6.5625}{24.265} = 0.27$
Life L_H [h]	(4.4.9), Page 20	$L_H = \frac{265}{pv} \cdot a_L = \frac{265}{0.27} \cdot 400 = 581$

Thrust washer

Given:			
Load Details	Axial Load	Inside Diameter D_i	38 mm
	Continuous Rotation	Outside Diameter D_o	62 mm
Shaft	Steel	Bearing Load F	6500 N
	Unlubricated at 25 °C	Rotational Speed N	10 1/min

Calculation Constants and Application Factors			
Specific Load Limit p_{lim}	140 MPa	(Table 8, Page 16)	
Application Factor a_T	1.0	(Table 10, Page 17)	
Material Application Factor a_M	1.0	(Table 11, Page 18)	
Bearing Size Factor a_B	0.85	(Fig. 21, Page 19)	
Life Correction Constant a_L	400	(Table 11, Page 18)	

Calculation	Ref	Value
Specific Load p [MPa]	(4.4.3), Page 20	$p = \frac{4 \cdot F}{\pi \cdot (D_o^2 - D_i^2)} = \frac{4 \cdot 6500}{\pi \cdot (62^2 - 38^2)} = 3.45$
Sliding Speed v [m/s]	(4.3.6), Page 16	$v = \frac{D_o + D_i}{2} \cdot \pi \cdot n = \frac{62 + 38}{2} \cdot \pi \cdot 10 = \frac{2 \cdot 60 \cdot 10^3}{60 \cdot 10^3} = 0.026$
High Load Factor a_E [-] (must be >0)	(4.4.4), Page 20	$a_E = \frac{p_{lim} - p}{p_{lim}} = \frac{140 - 3.45}{140} = 0.975$
Modified pv Factor [MPa x m/s]	(4.4.7), Page 20	$pv = \frac{3.34 \cdot 10^{-5} \cdot F \cdot n}{a_E \cdot (D_o - D_i) \cdot a_T \cdot a_M \cdot a_B} = \frac{2.171}{19.28} = 0.113$
Life L_H [h]	(4.4.12), Page 21	$L_H = \frac{175}{pv} \cdot a_L = \frac{175}{0.113} \cdot 400 = 1149$

Flanged Bush

Given:			
Load Details	Axial Load	Flange Outside Diameter D_H	23 mm
	Continuous Rotation	Inside Diameter D_i	15 mm
Shaft	Steel	Bearing Load F	250 N
	Unlubricated at 25 °C	Rotational Speed N	5 1/min

Calculation Constants and Application Factors			
Specific Load Limit p_{lim}	140 MPa	(Table 8, Page 16)	
Application Factor a_T	1.0	(Table 10, Page 17)	
Material Application Factor a_M	1.0	(Table 11, Page 18)	
Bearing Size Factor a_B	1.0	(Fig. 21, Page 19)	
Life Correction Constant a_L	400	(Table 11, Page 18)	

Calculation	Ref	Value
Specific Load p [MPa]	(4.4.2), Page 20	$p = \frac{F}{0.04 \cdot (D_H^2 - D_i^2)} = \frac{250}{0.04 \cdot (23^2 - 15^2)} = 20.55$
Sliding Speed v [m/s]	(4.3.6), Page 16	$v = \frac{D_H + D_i}{2} \cdot \pi \cdot n = \frac{23 + 15}{2} \cdot \pi \cdot 5 = \frac{2 \cdot 60 \cdot 10^3}{60 \cdot 10^3} = 0.005$
High Load Factor a_E [-] (must be >0)	(4.4.4), Page 20	$a_E = \frac{p_{lim} - p}{p_{lim}} = \frac{140 - 20.55}{140} = 0.0853$
Modified pv Factor [MPa x m/s]	(4.4.6), Page 20	$pv = \frac{6.5 \cdot 10^{-4} \cdot F \cdot n}{a_E \cdot (D_H - D_i) \cdot a_T \cdot a_M \cdot a_B} = \frac{0.8125}{6.82} = 0.119$
Life L_H [h]	(4.4.11), Page 21	$L_H = \frac{175}{pv} \cdot a_L = \frac{175}{0.119} \cdot 400 = 1071$

5 Lubrication

DP4 provides excellent performance in lubricated applications. The following sections describe the basics of lubrication

5.1 Lubricants

DP4 can be used with most fluids including:

- water
- lubricating oils
- engine oil

In general, the fluid will be acceptable if it does not chemically attack the filled PTFE overlay or the porous bronze interlayer.

Where there is doubt about the suitability of a fluid, a simple test is to submerge a sample of DP4 material in the fluid for two to three weeks at 15-20 °C above the operating temperature.

and provide guidance on the application of DP4 in such environments.

- turbine oil
- hydraulic fluid
- solvent
- refrigerants

The following will usually indicate that the fluid is not suitable for use with DP4:

- A significant change in the thickness of the DP4 material,
- A visible change in the bearing surface other than some discolouration or staining,
- A visible change in the microstructure of the bronze interlayer.

5.2 Tribology

There are three modes of lubricated bearing operation which relate to the thickness of the developed lubricant film between the bearing and the mating surface:

- Hydrodynamic lubrication
- Mixed film lubrication
- Boundary lubrication.

These three modes of operation depend upon:

- Bearing dimensions
- Clearance
- Load
- Speed
- Lubricant Viscosity
- Lubricant Flow

Hydrodynamic lubrication

Characterised by:

- Complete separation of the shaft from the bearing by the lubricant film
- Very low friction and no wear of the bearing or shaft since there is no contact
- Coefficients of friction of 0.001 to 0.01

Hydrodynamic conditions occur when

$$(5.2.1) \quad p \leq \frac{v \cdot \eta}{7.5} \cdot \frac{B}{D_i} \quad [\text{MPa}]$$

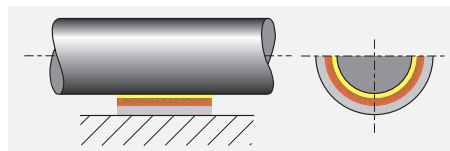


Fig. 24: Hydrodynamic lubrication

Mixed film lubrication

Characterised by:

- Combination of hydrodynamic and boundary lubrication.
- Part of the load is carried by localised areas of self pressurised lubricant and the remainder supported by boundary lubrication.
- Friction and wear depend upon the degree of hydrodynamic support developed.
- DP4 provides low friction and high wear resistance to support the boundary lubricated element of the load.

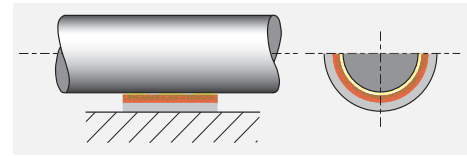


Fig. 25: Mixed film lubrication

Boundary lubrication

Characterised by:

- Rubbing of the shaft against the bearing with virtually no lubricant separating the two surfaces.
- Bearing material selection is critical to performance.
- Shaft wear is likely due to contact between bearing and shaft.
- The excellent properties of DP4 material minimises wear under these conditions.
- The dynamic coefficient of friction with DP4 is typically 0.05 to 0.3 under boundary lubrication conditions.
- The static coefficient of friction with DP4 is typically slightly above the dynamic coefficient of friction under boundary lubrication conditions.

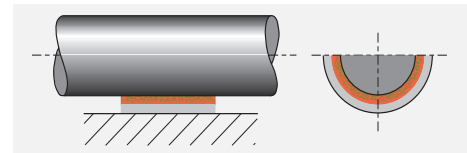


Fig. 26: Boundary lubrication

5.3 Characteristics of Lubricated Bearings

DP4 is particularly effective in the most demanding of lubricated applications

• High load conditions

In highly loaded applications operating under boundary or mixed film conditions DP4 shows excellent wear resistance and low friction.

• Start up and shut down under load

With insufficient speed to generate a hydrodynamic film the bearing will operate under boundary or mixed film conditions.

- DP4 minimises wear
- DP4 requires less start-up torque than conventional metallic bearings.

Note the following however:

If a DP4 bearing is required to run dry after running in water under non hydrodynamic conditions then the wear resistance will be substantially reduced due to an increased amount of bedding in wear.

In order to use Fig. 27

- Using the formula in Section 4:
 - Calculate the specific load p ,
 - Calculate the shaft surface speed v .

where full hydrodynamic operation cannot be maintained, for example:

• Sparse lubrication

Many applications require the bearing to operate with less than the ideal lubricant supply, typically with splash or mist lubrication only.

DP4 requires significantly less lubricant than conventional metallic bearings.

• Non lubricating fluids

DP4 operates satisfactorily in low viscosity and non lubricating fluids such as water and some process fluids.

Fig. 27, Page 25 shows the three lubrication regimes discussed above plotted on a graph of sliding speed vs the ratio of specific load to lubricant viscosity.

- Using the viscosity temperature relationships presented in Table 13:
 - Determine the viscosity in centipoise of the lubricant.

Note:

Viscosity is a function of operating temperature. If the operating temperature of the fluid is unknown, a provisional temperature of 25 °C above ambient can be used.

5.4 Design Guidance

Temperature [°C]	Dynamic viscosity η [cP]														
	0	10	20	30	40	50	60	70	80	90	100	110	120	130	140
Lubricant															
ISO VG 32	310	146	77	44	27	18	13	9.3	7.0	5.5	4.4	3.6	3.0	2.5	2.2
ISO VG 46	570	247	121	67	40	25	17	12	9.0	6.9	5.4	4.4	3.6	3.0	2.6
ISO VG 68	940	395	190	102	59	37	24	17	12	9.3	7.2	5.8	4.7	3.9	3.3
ISO VG 100	2110	780	335	164	89	52	33	22	15	11.3	8.6	6.7	5.3	4.3	3.6
ISO VG 150	3600	1290	540	255	134	77	48	31	21	15	11	8.8	7.0	5.6	4.6
Diesel oil	4.6	4.0	3.4	3.0	2.6	2.3	2.0	1.7	1.4	1.1	0.95				
Petrol	0.6	0.56	0.52	0.48	0.44	0.40	0.36	0.33	0.31						
Kerosene	2.0	1.7	1.5	1.3	1.1	0.95	0.85	0.75	0.65	0.60	0.55				
Water	1.79	1.30	1.0	0.84	0.69	0.55	0.48	0.41	0.34	0.32	0.28				

Table 13: Dynamic viscosity

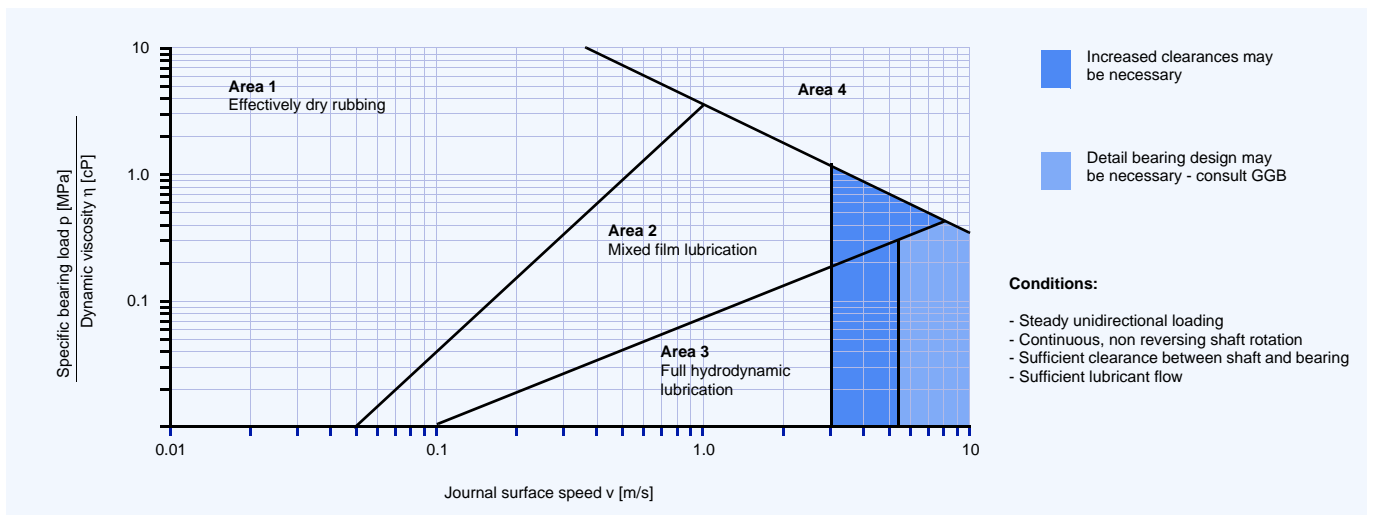


Fig. 27: Design guide for lubricated application

Explanation to Fig. 27

Area 1

The bearing will operate with boundary lubrication and p_v factor will be the major determinant of bearing life. DP4 bearing performance can be calculated using the

method given in Section 4, although the result will probably underestimate the bearing life.

Area 2

The bearing will operate with mixed film lubrication and p_v factor is no longer a significant parameter in determining the

bearing life. DP4 bearing performance will depend upon the nature of the fluid and the actual service conditions.

Area 3

The bearing will operate with hydrodynamic lubrication. Bearing wear will be determined only by the cleanliness of the

lubricant and the frequency of start up and shut down.

Area 4

These are the most demanding operating conditions. The bearing is operated under either high speed or high bearing load to viscosity ratio, or, a combination of both.

These conditions may cause

- excessive operating temperature and/or
- high wear rate.

Bearing performance may be improved by the addition of one or more grooves to the bearing and a shaft surface finish $<0.05 \mu\text{m } R_a$.

5.5 Clearances for lubricated operation

The recommended shaft and housing diameters given for standard DP4 bushes will provide sufficient clearance for applications operating with boundary lubrication.

For bearings operating with mixed film or hydrodynamic lubrication it may be

necessary to improve the fluid flow through the bearing by reducing the recommended shaft diameter by approximately 0.1 %, particularly when the shaft surface speed exceeds 2.5 m/s.

5.6 Grooving for lubricated operation

In demanding applications an axial oil groove will improve the performance of DP4. Fig. 28 shows the recommended form and location of a single groove with

respect to the applied load and the bearing split. GGB can manufacture special DP4 bearings with embossed or milled grooves on request.

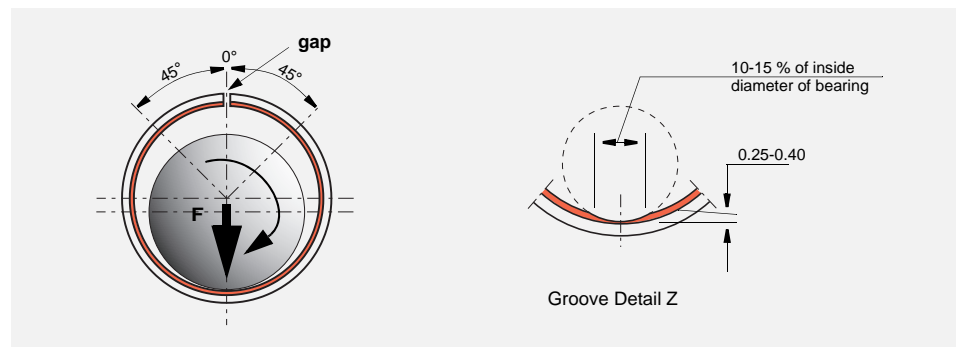


Fig. 28: Location of grooves

5.7 Mating Surface Finish for lubricated operation

- $R_a = 0.4 \pm 0.1 \mu\text{m}$ Boundary lubrication
- $R_a = 0.1 - 0.2 \mu\text{m}$ Mixed film or hydrodynamic conditions
- $R_a \leq 0.05 \mu\text{m}$ for the most demanding operating conditions.

5.8 Grease Lubrication

DP4 is not generally recommended for use with grease lubrication. In particular the following must be avoided:

- Dynamic loads - which can result in erosion of the PTFE bearing surface.
- Greases with EP additives or fillers such as graphite or MoS_2 which can cause rapid wear of DP4.

Under grease lubrication, improved performance can be obtained by the use of other GGB metal polymer bearing materials, for example, DX®, DX®10 with DuraStrong™ technology, DST™, HX™.

Please contact your local sales representative or consult www.ggbearings.com for more details.

6 Bearing Assembly

Dimensions and Tolerances

DP4 bushes are prefinished and excluding very exceptional circumstances, must not be broached, machined or otherwise modified in the bore. It is essential that the correct running clearance is used and that both the diameter of the shaft and the bore of the housing are finished to the limits given in the tables. Under dry running conditions any increase in the clearances given will result in a proportional reduction in performance.

If the bearing housing is unusually flexible the bush will not close in by the calculated

amount and the running clearance will be more than the optimum. In these circumstances the housing should be bored slightly undersize or the journal diameter increased, the correct size being determined by experiment.

Where free running is essential, or where light loads (less than 0.1 MPa) prevail and the available torque is low, increased clearance is required and it is recommended that the shaft size quoted in the table be reduced by 0.025 mm.

6.1 Allowance for Thermal Expansion

For operation in high temperature environments the clearance should be increased by the amounts indicated by Fig. 29 to

compensate for the inward thermal expansion of the bearing lining.

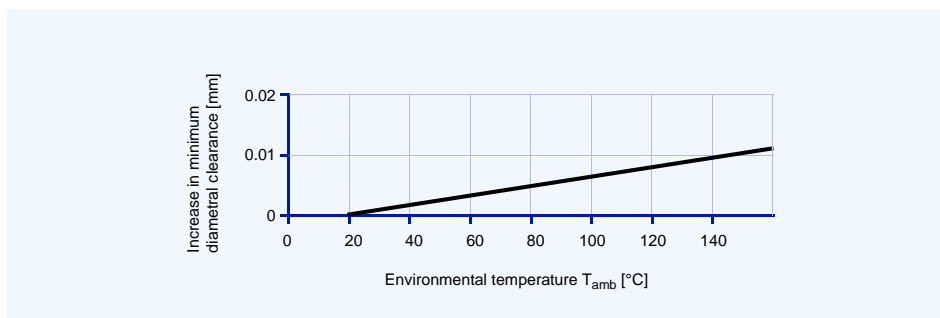


Fig. 29: Increase in diametral clearance

If the housing is non-ferrous then the bore should be reduced by the amounts given in Table 14, in order to give an increased

interference fit to the bush, with a similar reduction in the journal diameter additional to that indicated by Fig. 29.

Housing material	Reduction in housing diameter per 100 °C rise	Reduction in shaft diameter per 100 °C rise
Aluminium alloys	0.1 %	0.1 % + values from Fig. 29
Copper base alloys	0.05 %	0.05 % + values from Fig. 29
Steel and cast iron	–	values from Fig. 29
Zinc base alloys	0.15 %	0.15 % + values from Fig. 29

Table 14: Allowance for high temperature

6.2 Tolerances for minimum clearance

Where it is required to keep the variation of assembled clearance to a minimum, closer tolerances can be specified towards the

upper end of the journal tolerance and the lower end of the housing tolerance.

If housings to H6 tolerance are used, then the journals should be finished to the following limits.

D_i	D_j
>5 mm <25 mm	-0.019 to -0.029
>25 mm < 50 mm	-0.021 to -0.035

Table 15: Shaft tolerances for use with H6 housings

The sizes in Table 16 give the following nominal clearance range.

D_i	C_D
10 mm	0,009 to 0,080
50 mm	0,011 to 0,134

Table 16: Clearance vs bearing diameter

Burnishing

The burnishing of the bore of an assembled DP4 bush enables a smaller clearance variation to be obtained. Fig. 30 shows a recommended burnishing tool design for the burnishing of DP4 bushes.

The coining section of the burnishing tool should be case hardened (case depth 0.6-1.2 mm, HRC 60±2) and polished with diamond paste ($R_z = 1 \mu\text{m}$). A TiN type surface treatment increases the wear resistance of the burnishing tool and when absent gives a visual indication of burnishing tool wear.

The reduction in bearing performance as a result of burnishing is allowed for in the bearing life calculation by the application factor a_C (Table 12, Page 19). The impact of burnishing on the bearing and assembly should be validated by trials.

Note: Ball burnishing or fine boring of DP4 bushes is not recommended.

Assembled bush Inside- \varnothing	Required bush Inside- \varnothing	Required burnishing tool- $\varnothing D_C$
$D_{i,a}$	$D_{i,a} + 0.025$	$D_{i,a} + 0.06$
$D_{i,a}$	$D_{i,a} + 0.038$	$D_{i,a} + 0.08$
$D_{i,a}$	$D_{i,a} + 0.050$	$D_{i,a} + 0.1$

Table 17: Burnishing Tool Tolerances

The values given in Table 17 indicate the dimensions of the burnishing tool required to give specific increases in the bearing bore diameter.

Exact values must be determined by test.

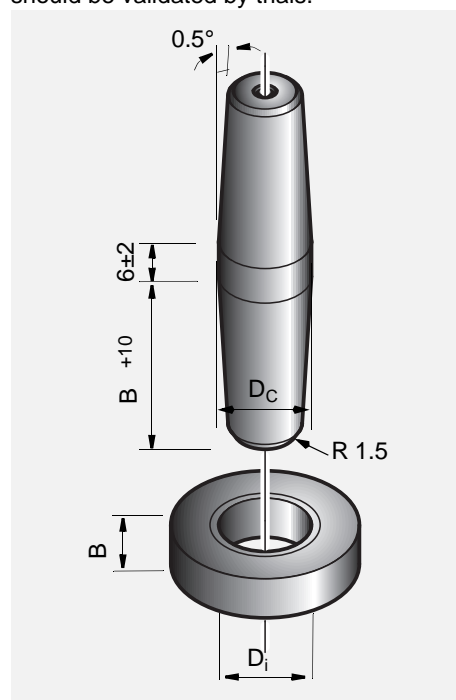


Fig. 30: Burnishing Tool

6.3 Counterface Design

The suitability of mating surface materials and recommendations of mating surface finish for use with DP4 are discussed in detail on page 16.

DP4 is normally used in conjunction with ferrous journals and thrust faces, but in damp or corrosive surroundings, particularly without the protection of oil or grease, stainless steel, hard chromium plated mild steel, or hard anodised aluminium is recommended. When plated mating surfaces are specified the plating should possess adequate strength and adhesion,

particularly if the bearing is to operate with high fluctuating loads.

The shaft or thrust collar used in conjunction with the DP4 bush or thrust washer must extend beyond the bearing surface in order to avoid cutting into it. The mating surface must also be free from grooves or flats, the end of the shaft should be given a lead-in chamfer and all sharp edges or projections which may damage the soft overlay of the DP4 must be removed.

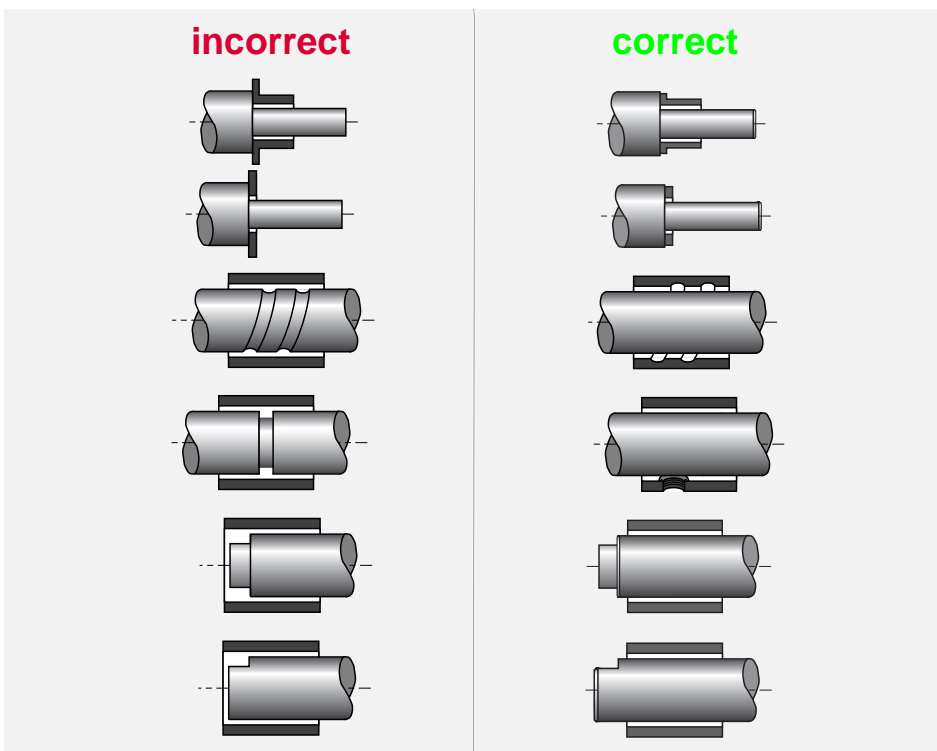


Fig. 31: Counterface design

6.4 Installation

Fitting of cylindrical Bushes

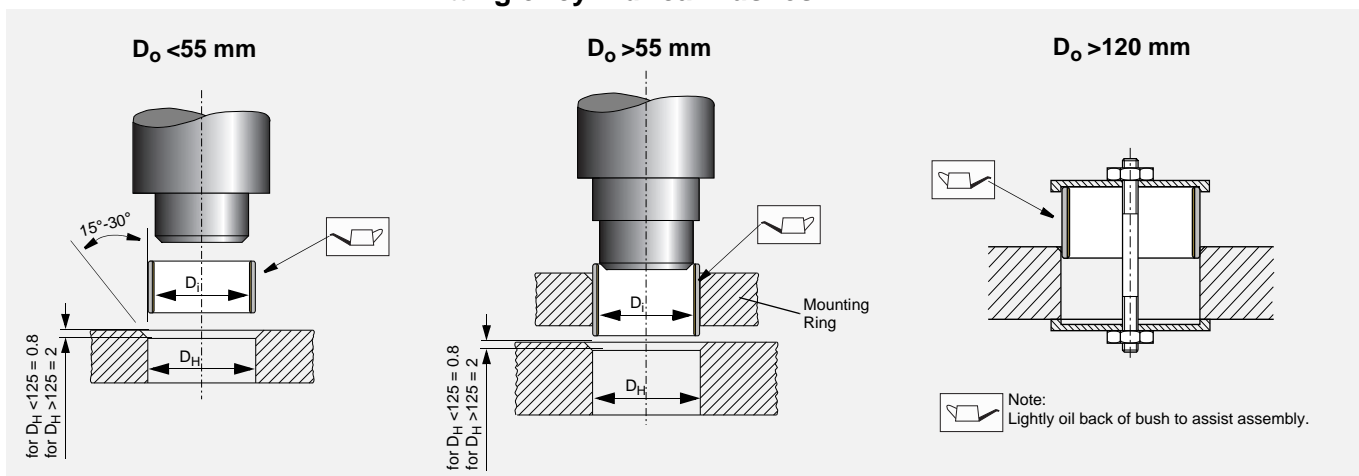


Fig. 32: Fitting of cylindrical bushes

Fitting of flanged bushes

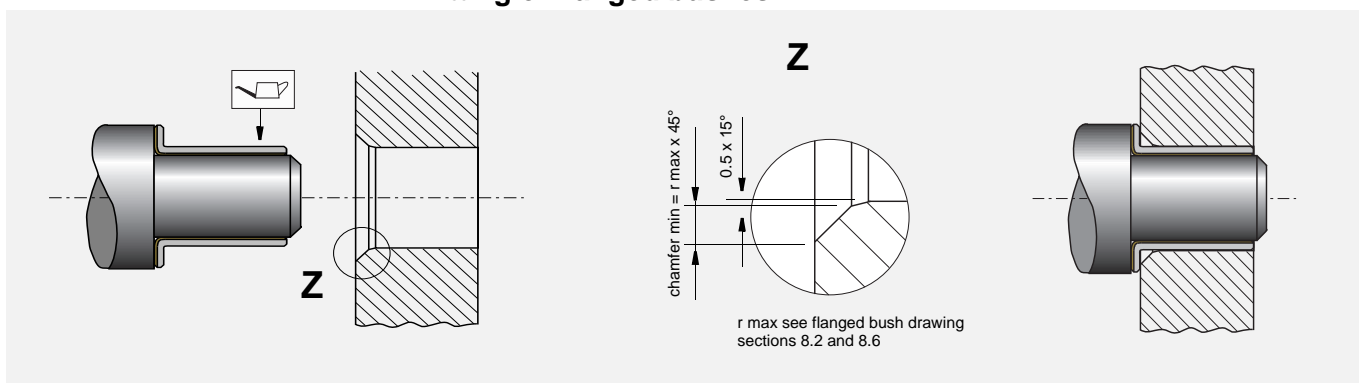


Fig. 33: Fitting of flanged bushes

Insertion Forces

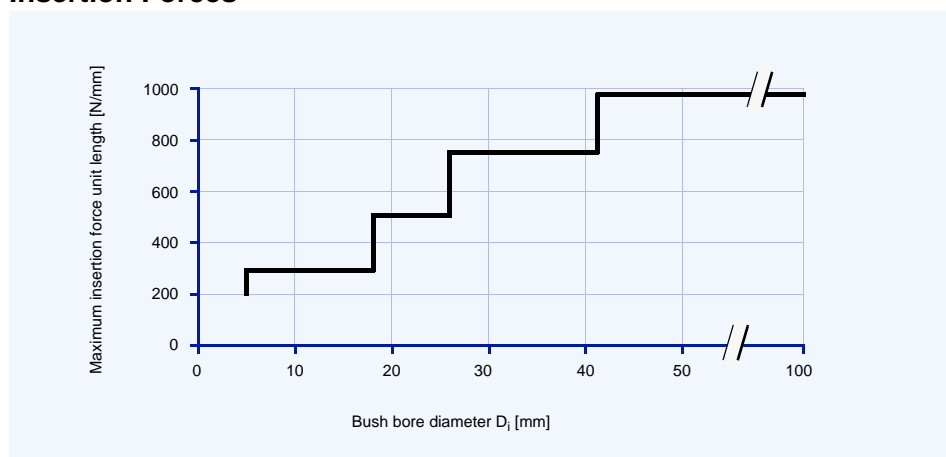


Fig. 34: Maximum insertion force F_i

Alignment

Accurate alignment is an important consideration for all bearing assemblies. With DP4 bearings misalignment over the

length of a bush (or pair of bushes), or over the diameter of a thrust washer should not exceed 0.020 mm as illustrated in Fig. 35.

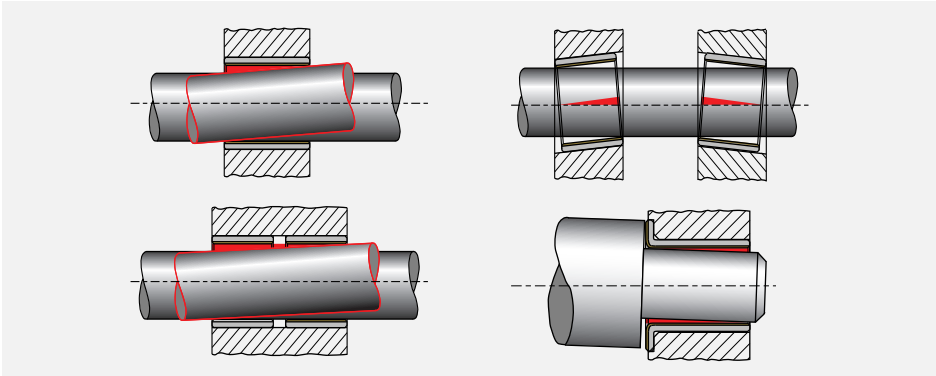


Fig. 35: Alignment

Sealing

While DP4 can tolerate the ingress of some contaminant materials into the bearing without loss of performance, where there is the possibility of highly

abrasive material entering the bearing, a suitable sealing arrangement, as illustrated in Fig. 36 should be provided.

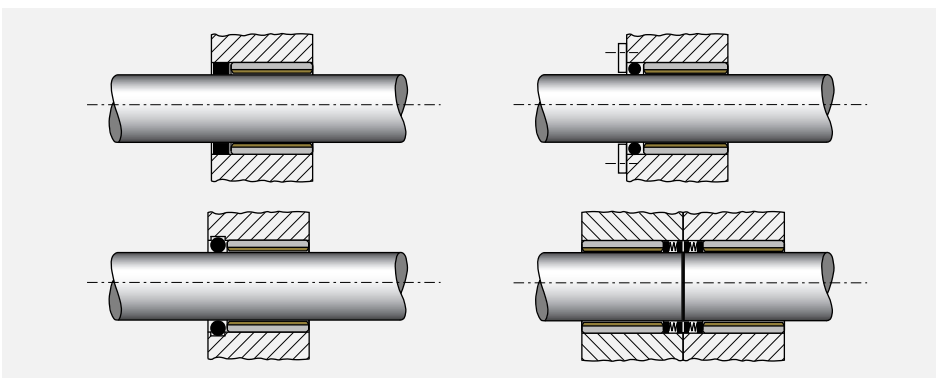


Fig. 36: Recommended sealing arrangements

6.5 Axial Location

Where axial location is necessary, it is advisable to fit DP4 thrust washers in

conjunction with DP4 bushes, even when the axial loads are low.

Fitting of Thrust Washers

DP4 thrust washers should be located in a recess as shown in Fig. 37. For the recess diameter the tolerance class [D10] is recommended. The recess depth is given in the product tables, page 40 and following.

If a recess is not possible one of the following methods may be used:

- Two dowel pins
- Two screws
- Adhesive
- Soldering (temperature <320 °C).

Important Note

- Ensure the washer ID does not touch the shaft after assembly
- Ensure that the washer is mounted with the steel/bronze backing to the housing
- Dowel pins should be recessed 0.25 mm below the bearing surface
- Screws should be countersunk 0.25 mm below the bearing surface
- DP4 must not be heated above 320 °C
- Contact adhesive manufacturers for guidance selection of suitable adhesives
- Protect the bearing surface to prevent contact with adhesive.

Grooves for Wear Debris Removal

Tests with thrust washers have demonstrated that for optimum dry wear performance at specific loads in excess of 35 MPa, four wear debris removal grooves should be machined in the bearing surface as shown in Fig. 38.

Grooves in bushes have not been found to be beneficial in this respect.

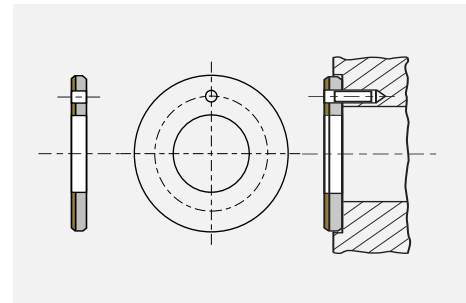


Fig. 37: Installation of Thrust-Washer

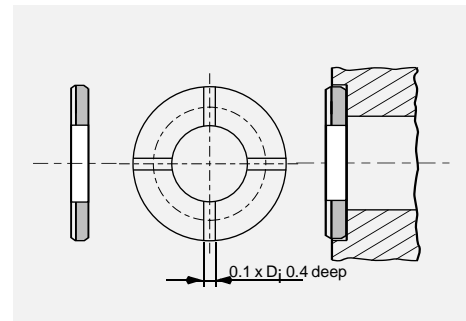


Fig. 38: Debris removal Grooves

Slideways

DP4 strip material for use as slideway bearings should be installed using one of the following methods:

- Countersunk screws
- Adhesives
- Mechanical location as shown in Fig. 39.

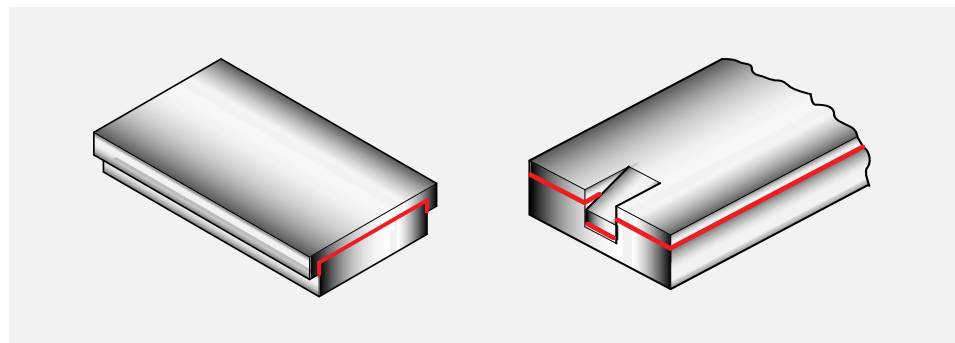


Fig. 39: Mechanical location of DP4 slideplates

7 Modification

7.1 Cutting and Machining

The modification of DP4 bearing components requires no special procedures. In general it is more satisfactory to perform machining or drilling operations from the PTFE side in order to avoid burrs. When cutting is done from the steel side, the

minimum cutting pressure should be used and care taken to ensure that any steel or bronze particles protruding into the remaining bearing material, and all burrs, are removed.

Drilling Oil Holes

Bushes should be adequately supported during the drilling operation to ensure that

no distortion is caused by the drilling pressure.

Cutting Strip Material

DP4 strip material may be cut to size by any one of the following methods.

Care must be taken to protect the bearing surface from damage and to ensure that no deformation of the strip occurs:

- Using side and face cutter, or slitting saw, with the strip held flat and securely

on a horizontal milling machine.

- Cropping
- Guillotine (For widths less than 90 mm only)
- Water-jet cutting
- Laser cutting (see Health Warning).

7.2 Electroplating

DP4 Components

In order to provide some protection in mildly corrosive environments the steel back and end faces of standard range DP4 bearings are tin flashed.

DP4 can be electroplated with most of the conventional electroplating metals including the following:


- zinc ISO 2081
- nickel ISO 1456
- hard chromium ISO 1456.

For the harder materials if the specified plating thickness exceeds approximately 5 μm then the housing diameter should be increased by twice the plating thickness in order to maintain the correct assembled bearing bore size.

Where electrolytic attack is possible tests should be conducted to ensure that all the materials in the bearing environment are mutually compatible.

8 Standard Products

8.1 DP4 Cylindrical bushes

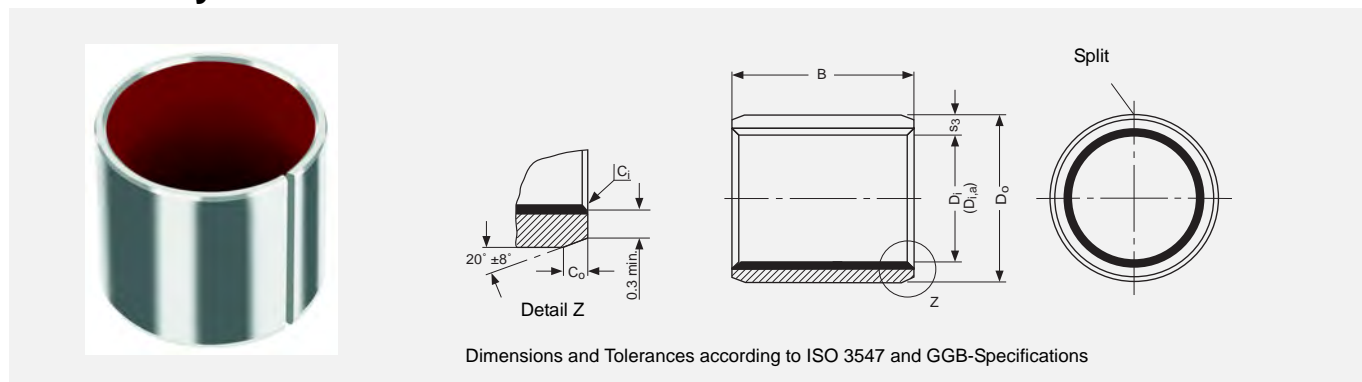

Dimensions and Tolerances according to ISO 3547 and GGB-Specifications

All dimensions in mm

Outside C₀ and Inside C_i chamfers

Wall thickness s ₃	C ₀ (a)		C _i (b)
	machined	rolled	
0.75	0.5 ± 0.3	0.5 ± 0.3	-0.1 to -0.4
1	0.6 ± 0.4	0.6 ± 0.4	-0.1 to -0.5
1.5	0.6 ± 0.4	0.6 ± 0.4	-0.1 to -0.7

Wall thickness s ₃	C ₀ (a)		C _i (b)
	machined	rolled	
2	1.2 ± 0.4	1.0 ± 0.4	-0.1 to -0.7
2.5	1.8 ± 0.6	1.2 ± 0.4	-0.2 to -1.0

a = Chamfer C₀ machined or rolled at the option of the manufacturer

b = C_i can be a radius or a chamfer in accordance with ISO 13715

Part No.	Nominal Diameter		Wall thickness s ₃	Width B	Shaft-∅ D _J [h6, f7, h8]		Housing-∅ D _H [H6, H7]		Bush-∅ D _{i,a} Ass. in H6/H7 housing	Clearance C _D						
	D _i	D _O			max. min.	max. min.	max. min.	max. min.	max. min.							
0203DP4	2	3.5	0.750 0.730	3.25	h6	2.000 1.994	H6	3.508 3.500	2.048 2.000	0.054 0.000						
0205DP4				5.25							4.75					
0303DP4	3	4.5		3.25							h6	3.000 2.994	H6	4.508 4.500	3.048 3.000	
0305DP4				5.25												4.75
0306DP4				6.25												5.75
0403DP4	4	5.5		3.25							h6	4.000 3.992	H6	5.508 5.500	4.048 4.000	
0404DP4				4.25	3.75											
0406DP4				6.25	5.75											
0410DP4				10.25	9.75											
0505DP4	5	7		5.25	h6	4.990 4.978	H6	7.015 7.000	5.055 4.990							
0508DP4				8.25							7.75					
0510DP4				10.25							9.75					
0604DP4	6	8	4.25	f7	5.990 5.978	H7	8.015 8.000	6.055 5.990								
0606DP4			3.75						7.75							
0608DP4			6.25						5.75							
0610DP4			7.75						7.75							
0705DP4			10.25						9.75							
0710DP4	7	9	5.25	h6	6.987 6.972	H6	9.015 9.000	7.055 6.990								
0710DP4			4.75						10.25	9.75						

Part No.	Nominal Diameter		Wall thickness S ₃	Width B	Shaft-∅ D _J [h6, f7, h8]	Housing-∅ D _H [H6, H7]	Bush-∅ D _{I,a} Ass. in H6/H7 housing	Clearance C _D			
	D _i	D _o							max. min.	max. min.	max. min.
0806DP4	8	10	1.005 0.980	6.25	f7	H7	7.987 7.972	10.015 10.000	8.055 7.990	0.083 0.003	
0808DP4				5.75							8.25
0810DP4				7.75							10.25
0812DP4				9.75							12.25
1006DP4				11.75							6.25
1008DP4	5.75	8.25									
1010DP4	7.75	10.25									
1012DP4	9.75	12.25									
1015DP4	11.75	15.25									
1020DP4	14.75	20.25									
1208DP4	12	14		19.75			11.984 11.966	14.018 14.000	12.058 11.990	0.086 0.003	
1210DP4				8.25							10.25
1212DP4				7.75							9.75
1215DP4				12.25							11.75
1220DP4				14.75							15.25
1225DP4				19.75							20.25
1310DP4				13							15
1320DP4	10.25	9.75									
1405DP4	14	16		20.25			13.984 13.966	16.018 16.000	14.058 13.990	0.092 0.006	
1410DP4				5.25							4.75
1412DP4			10.25	9.75							
1415DP4			12.25	11.75							
1420DP4			14.75	15.25							
1425DP4			19.75	20.25							
1510DP4			15	17	24.75	14.984 14.966					17.018 17.000
1512DP4	10.25	9.75									
1515DP4	12.25	11.75									
1520DP4	14.75	15.25									
1525DP4	19.75	20.25									
1610DP4	16	18	24.75	15.984 15.966	18.018 18.000	16.058 15.990	0.092 0.006				
1612DP4			10.25					9.75			
1615DP4			12.25					11.75			
1620DP4			14.75					15.25			
1625DP4			19.75					20.25			
1720DP4	17	19	19.75	16.984 16.966	19.021 19.000	17.061 16.990	0.095 0.006				

8 Standard Products

Part No.	Nominal Diameter		Wall thickness s_3	Width B	Shaft- \varnothing D_J [h6, f7, h8]		Housing- \varnothing D_H [H6, H7]		Bush- \varnothing $D_{i,a}$ Ass. in H6/H7 housing		Clearance C_D
	D_i	D_o			max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	
1810DP4	18	20	1.005 0.980	10.25	17.984 17.966	20.021 20.000	18.061 17.990	0.095 0.006			
1815DP4				9.75							
1820DP4				15.25							
1825DP4				14.75							
2010DP4				20.25							
2015DP4	19.75										
2020DP4	20	23	1.505 1.475	25.25	19.980 19.959	23.021 23.000	20.071 19.990	0.112 0.010			
2025DP4				24.75							
2030DP4				30.25							
2215DP4				29.75							
2220DP4				15.25							
2225DP4	14.75										
2230DP4	22	25	1.505 1.475	20.25	21.980 21.959	25.021 25.000	22.071 21.990	0.112 0.010			
2415DP4				19.75							
2420DP4				25.25							
2425DP4				24.75							
2430DP4				30.25							
2515DP4	24	27	1.505 1.475	29.75	23.980 23.959	27.021 27.000	24.071 23.990	0.112 0.010			
2520DP4				15.25							
2525DP4				14.75							
2530DP4				20.25							
2550DP4				19.75							
2815DP4	25	28	2.005 1.970	25.25	24.980 24.959	28.021 28.000	25.071 24.990	0.126 0.010			
2820DP4				24.75							
2825DP4				30.25							
2830DP4				29.75							
3010DP4				15.25							
3015DP4	14.75										
3020DP4	30	34	2.005 1.970	20.25	29.980 29.959	34.025 34.000	30.085 29.990	0.126 0.010			
3025DP4				19.75							
3030DP4				25.25							
3040DP4				24.75							
3220DP4				30.25							
3230DP4	32	36	2.005 1.970	29.75	31.975 31.950	36.025 36.000	32.085 31.990	0.135 0.015			
3240DP4				40.25							
				39.75							


Part No.	Nominal Diameter		Wall thickness S ₃	Width B	Shaft-∅ D _J [h6, f7, h8]	Housing-∅ D _H [H6, H7]	Bush-∅ D _{I,a} Ass. in H6/H7 housing	Clearance C _D
	D _i	D _o						
3520DP4	35	39	2.005 1.970	20.25	34.975 34.950	39.025 39.000	35.085 34.990	0.135 0.015
3530DP4				19.75				
3535DP4				30.25				
3540DP4				29.75				
3550DP4				35.25 34.75				
3720DP4				40.25 39.75				
4020DP4	40	44	2.005 1.970	50.25	36.975 36.950	41.025 41.000	37.085 36.990	0.135 0.015
4030DP4				49.75				
4040DP4				20.25 19.75				
4050DP4				30.25				
4520DP4				29.75				
4530DP4				39.975 39.950				
4540DP4	45	50	2.505 2.460	40.25	44.975 44.950	50.025 50.000	40.085 39.990	0.155 0.015
4545DP4				39.75				
4550DP4				45.25 44.75				
5020DP4				50.25 49.75				
5030DP4				20.25 19.75				
5040DP4				30.25 29.75				
5050DP4	50	55	2.505 2.460	40.25	49.975 49.950	55.030 55.000	50.110 49.990	0.160 0.015
5060DP4				39.75				
5520DP4				50.25 49.75				
5525DP4				60.25 59.75				
5530DP4				20.25 19.75				
5540DP4				25.25 24.75				
5550DP4	55	60	2.505 2.460	30.25	54.970 54.940	60.030 60.000	55.110 54.990	0.170 0.020
5555DP4				29.75				
5560DP4				40.25 39.75				
6020DP4				50.25 49.75				
6030DP4				55.25 54.75				
6040DP4				60.25 59.75				
6050DP4	60	65	2.505 2.460	20.25	59.970 59.940	65.030 65.000	60.110 59.990	0.170 0.020
6060DP4				19.75				
6070DP4				30.25				
				29.75				
				40.25 39.75				
				50.25 49.75				

8 Standard Products

Part No.	Nominal Diameter		Wall thickness S ₃	Width B	Shaft-∅ D _J [h6, f7, h8]	Housing-∅ D _H [H6, H7]	Bush-∅ D _{i,a} Ass. in H6/H7 housing	Clearance C _D			
	D _i	D _O							max. min.	max. min.	max. min.
6530DP4	65	70	2.505 2.460	30.25	f7	70.030 70.000	65.110 64.990	0.170 0.020			
6550DP4				29.75					64.970		
6570DP4				50.25					64.940		
7040DP4	70	75		70.25					69.970	75.030	70.110
7050DP4	49.75	69.940		75.000					69.990		
7070DP4	70.25	75.000		69.990							
7560DP4	75	80		40.25	H7	80.030 80.000	75.110 74.990				
7580DP4				39.75					74.970		
8040DP4				50.25					74.940		
8060DP4	80	85		70.25					85.035	80.155	
8080DP4	49.75	79.954		85.000					80.020		
80100DP4	70.25	85.000		79.950					80.020		
8530DP4	85	90	60.25	h8	90.035 90.000	85.155 85.020					
8560DP4			59.75				85.000				
85100DP4			80.25				84.946				
9060DP4	90	95	79.75				95.035	90.155			
90100DP4	100.50	89.946	95.000				90.020				
9560DP4	99.50	94.946	95.000				95.020				
10050DP4	95	100	30.50	H7	100.035 100.000	95.155 95.020					
10060DP4			29.50				100.000				
100115DP4			60.50				99.946				
10560DP4	100	105	59.50				105.035	100.155			
105115DP4	100.50	104.946	105.000				100.020				
11060DP4	99.50	109.946	105.000				105.020				
11550DP4	105	110	60.50	h8	110.035 110.000	105.155 105.020					
11570DP4			59.50				105.000				
12050DP4			110				115	115.50	115.035	110.155	
12060DP4	110.50	109.946	115.000				110.020				
120100DP4	114.50	114.50	115.000				115.020				
125100DP4	114.50	114.50	110.000				115.020				
13060DP4	115	120	50.50	H7	120.035 120.000	115.155 115.020					
130100DP4			49.50				115.000				
12050DP4			110				115	115.000	115.020		
12060DP4	120	125	115.50				120.035	115.155			
120100DP4	100.50	119.946	115.000				120.000				
125100DP4	99.50	125.000	115.000				120.000				
13060DP4	125	130	60.50	h8	125.040 125.000	120.210 120.070					
130100DP4			49.50				125.000				
13060DP4			100.50				124.937				
13060DP4	120	125	100.50				130.040	125.210			
130100DP4	99.50	129.937	130.000				125.070				
130100DP4	100.50	129.937	130.000				130.070				

Part No.	Nominal Diameter		Wall thickness s_3		Width B		Shaft- \varnothing D_J [h6, f7, h8]		Housing- \varnothing D_H [H6, H7]		Bush- \varnothing $D_{i,a}$ Ass. in H6/H7 housing		Clearance C_D	
	D_i	D_o	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	
13560DP4	135	140	2.465 2.415	60.50	h8	H7	135.000 134.937	140.040 140.000	135.210 135.070	0.273 0.070				
13580DP4				80.50							60.50			
14060DP4				79.50							59.50			
140100DP4	140	145		60.50			140.000 139.937	145.040 145.000	140.210 140.070					
15060DP4				59.50							60.50			
15080DP4				79.50							59.50			
150100DP4	150	155		80.50			150.000 149.937	155.040 155.000	150.210 150.070					
16080DP4				79.50							60.50			
160100DP4				99.50							59.50			
180100DP4	180	185		80.50			160.000 159.937	165.040 165.000	160.210 160.070					
200100DP4	200	205		79.50										
210100DP4	210	215		100.50										
220100DP4	220	225		99.50			180.000 179.937	185.046 185.000	180.216 180.070					
250100DP4	250	255		200.000										
300100DP4	300	305		199.928										
				210.000	205.046 205.000	200.216 200.070								
				209.928										
				220.000										
				219.928	215.046 215.000	210.216 210.070								
				225.000										
				225.046										
				225.000	225.046 225.000	220.216 220.070								
				250.000										
				249.928										
				250.000	255.052 255.000	250.222 250.070								
				300.000										
				299.919										
				305.000	305.052 305.000	300.222 300.070								

8.2 DP4 Flanged bushes

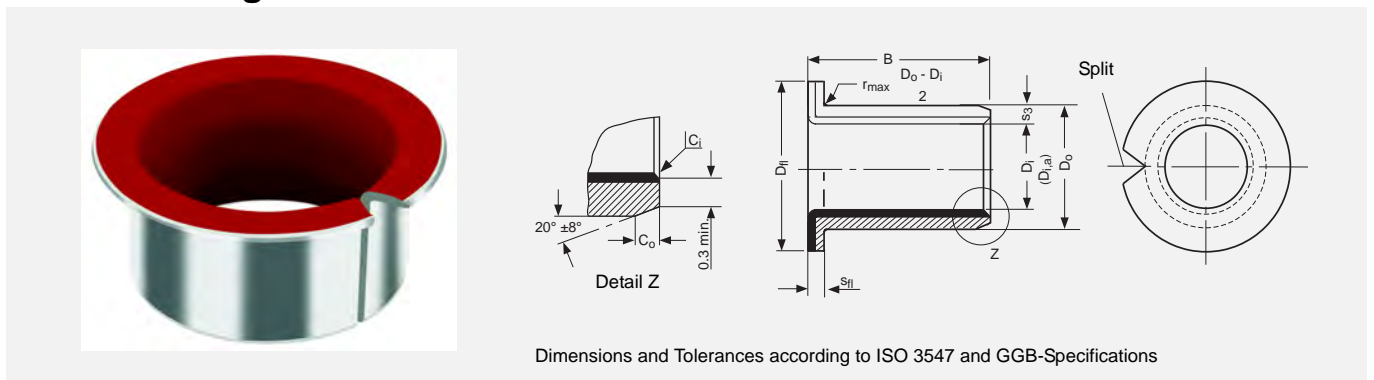

All dimensions in mm

Outside C_0 and Inside C_1 chamfers

Wall thickness s_3	C_0 (a)		C_1 (b)
	machined	rolled	
0.75	0.5 ± 0.3	0.5 ± 0.3	-0.1 to -0.4
1	0.6 ± 0.4	0.6 ± 0.4	-0.1 to -0.5
1.5	0.6 ± 0.4	0.6 ± 0.4	-0.1 to -0.7

Wall thickness s_3	C_0 (a)		C_1 (b)
	machined	rolled	
2	1.2 ± 0.4	1.0 ± 0.4	-0.1 to -0.7
2.5	1.8 ± 0.6	1.2 ± 0.4	-0.2 to -1.0

a = Chamfer C_0 machined or rolled at the option of the manufacturer


b = C_1 can be a radius or a chamfer in accordance with ISO 13715

Part No.	Nominal Diameter		Wall thickness s_3		Flange thickness s_{fl}		Flange- \varnothing D_H		Width B		Shaft- \varnothing D_J [h6, f7]		Housing- \varnothing D_H [H6, H7]		Bush- \varnothing $D_{i,a}$ Ass. in H6/H7 housing		Clearance C_D	
	D_i	D_o	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	
BB0304DP4	3	4.5	0.750 0.730	0.80 0.70	7.50	4.25	h6	3.000 2.994	H6	4.508 4.500	3.048 3.000	0.054 0.000						
BB0404DP4	4	5.5			6.50								3.75	4.000 3.992	4.048 4.000	0.056 0.000		
BB0505DP4	5	7	1.005 0.980	1.05 0.80	10.50 9.50	5.25 4.75	f7	4.990 4.978	H7	7.015 7.000	5.055 4.990	0.077 0.000						

8 Standard Products

Part No.	Nominal Diameter		Wall thickness s ₃	Flange thickness s _{fl}	Flange-Ø D _{fl}	Width B	Shaft-Ø D _J [h6, f7]	Housing-Ø D _H [H6, H7]	Bush-Ø D _{I,a} Ass. in H6/H7 housing	Clearance C _D						
	D _i	D _o									max. min.	max. min.	max. min.	max. min.	max. min.	max. min.
BB0604DP4	6	8	1.005 0.980	1.05 0.80	12.50	4.25	f7	H7	6.055 5.990	0.077 0.000						
BB0608DP4						3.75										
BB0806DP4	8	10			15.50	8.25					7.987	10.015	8.055			
BB0808DP4						7.75										
BB0810DP4					18.50	5.75					9.987	12.018	10.058			
BB1007DP4						5.25										
BB1009DP4	10	12			17.50	7.75					9.972	12.000	9.990			
BB1012DP4						7.25										
BB1017DP4					20.50	9.75								11.984	14.018	12.058
BB1207DP4						9.25										
BB1209DP4	12	14			19.50	6.75					11.966	14.000	11.990			
BB1212DP4						8.75										
BB1217DP4					22.50	12.25								13.984	16.018	14.058
BB1412DP4						11.75										
BB1417DP4	14	16			21.50	12.25					13.966	16.000	13.990			
BB1509DP4						11.75										
BB1512DP4					23.50	9.25								14.984	17.018	15.058
BB1517DP4						8.75										
BB1612DP4	16	18			24.50	12.25					15.984	18.018	16.058			
BB1617DP4						11.75										
BB1812DP4			26.50	12.25	17.984	20.021	18.061									
BB1817DP4				11.75												
BB1822DP4	18	20	25.50	17.25	17.966	20.000	17.990									
BB2012DP4				16.75												
BB2017DP4			30.50	12.25				19.980	23.021	20.071						
BB2022DP4				11.25												
BB2512DP4	25	28	35.50	16.75	24.980	28.021	25.071									
BB2517DP4				16.25												
BB2522DP4			42.50	21.75				29.980	34.025	30.085						
BB3016DP4				21.25												
BB3026DP4	30	34	41.50	16.25	29.959	34.000	29.990									
BB3516DP4				15.75												
BB3526DP4			47.50	26.25				34.975	39.025	35.085						
BB4016DP4				25.75												
BB4026DP4	40	44	53.50	16.25	39.975	44.025	40.085									
BB4516DP4				15.75												
BB4526DP4			58.50	26.25				44.975	50.025	45.105						
BB4526DP4				25.75												

8.3 DP4 Flanged Washers

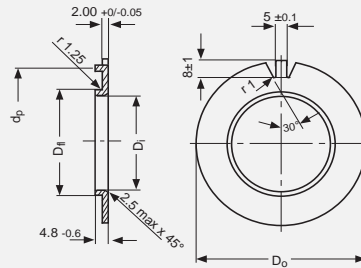

All dimensions in mm


Part No.	Inside- \varnothing D_i	Outside- \varnothing D_o	Flange- \varnothing D_{fl}	Location- \varnothing d_p
	max. min.	max. min.	max. min.	max. min.
BS40DP4	40.70	75.0	44.00	65.5
	40.20	74.5	43.90	64.5
BS50DP4	51.50	85.0	55.00	75.5
	51.00	84.5	54.88	74.5
BS60DP4	61.50	95.0	65.00	85.5
	61.00	94.5	64.88	84.5
BS70DP4	71.50	110.0	75.00	100.5
	71.00	109.5	74.88	99.5
BS80DP4	81.50	120.0	85.00	110.5
	81.00	119.5	84.86	109.5
BS90DP4	91.50	130.0	95.00	120.5
	91.00	129.5	94.86	119.5
BS100DP4	101.50	140.0	105.00	130.5
	101.00	139.5	104.86	129.5

Corrosion Protection: Washers will be supplied covered with a light coating of oil.

Tab (Lug) Form: Washers are supplied with this feature in an unformed state (Flat). This feature may be supplied in the formed state only when requested by the customer.

8 Standard Products


8.4 DP4 Thrust Washers

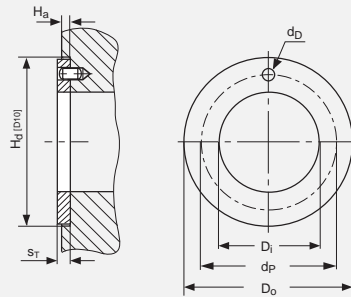

All dimensions in mm

Part No.	Inside- \varnothing D_i		Outside- \varnothing D_o	Thickness s_T	Dowel Hole		Recess Depth H_a
	min.	max.			$\varnothing d_D$	PCD- $\varnothing d_P$	
			max. min.	max. min.	max. min.	max. min.	max. min.
WC08DP4	10.00	10.25	20.00 19.75	1.50 1.45	No Hole	No Hole	1.20 0.95
WC10DP4	12.00	12.25	24.00 23.75		1.875 1.625	18.12 17.88	
WC12DP4	14.00	14.25	26.00 25.75		2.375 2.125	20.12 19.88	
WC14DP4	16.00	16.25	30.00 29.75			22.12 21.88	
WC16DP4	18.00	18.25	32.00 31.75		3.375 3.125	25.12 24.88	
WC18DP4	20.00	20.25	36.00 35.75			28.12 27.88	
WC20DP4	22.00	22.25	38.00 37.75		4.375 4.125	30.12 29.88	
WC22DP4	24.00	24.25	42.00 41.75			33.12 32.88	
WC24DP4	26.00	26.25	44.00 43.75		61.12 60.88	35.12 34.88	
WC25DP4	28.00	28.25	48.00 47.75			38.12 37.88	
WC30DP4	32.00	32.25	54.00 53.75		65.12 64.88	43.12 42.88	
WC35DP4	38.00	38.25	62.00 61.75			50.12 49.88	
WC40DP4	42.00	42.25	66.00 65.75		76.12 75.88	54.12 53.88	
WC45DP4	48.00	48.25	74.00 73.75			61.12 60.88	
WC50DP4	52.00	52.25	78.00 77.75	1.70 1.45	65.12 64.88		
WC60DP4	62.00	62.25	90.00 89.75		76.12 75.88		

8.5 DP4B Cylindrical bushes

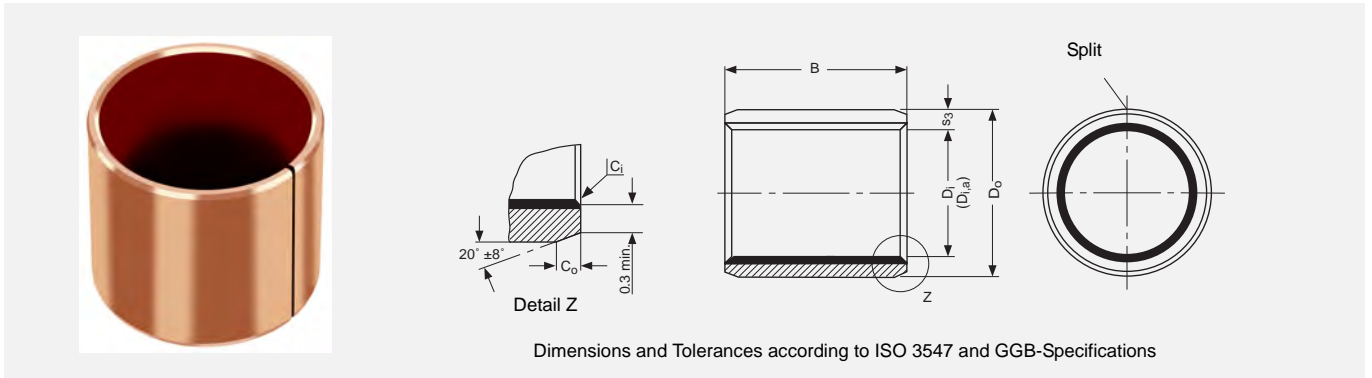

Dimensions and Tolerances according to ISO 3547 and GGB-Specifications

All dimensions in mm

Outside C₀ and Inside C_i chamfers

Wall thickness s ₃	C ₀ (a)		C _i (b)
	machined	rolled	
0.75	0.5 ± 0.3	0.5 ± 0.3	-0.1 to -0.4
1	0.6 ± 0.4	0.6 ± 0.4	-0.1 to -0.5
1.5	0.6 ± 0.4	0.6 ± 0.4	-0.1 to -0.7

Wall thickness s ₃	C ₀ (a)		C _i (b)
	machined	rolled	
2	1.2 ± 0.4	1.0 ± 0.4	-0.1 to -0.7
2.5	1.8 ± 0.6	1.2 ± 0.4	-0.2 to -1.0

a = Chamfer C₀ machined or rolled at the option of the manufacturer

b = C_i can be a radius or a chamfer in accordance with ISO 13715


Part No.	Nominal Diameter		Wall thickness s ₃	Width B	Shaft-∅ D _J [h6, f7, h8]	Housing-∅ D _H [H6, H7]		Bush-∅ D _{i,a} ass. in H6/H7 housing	Clearance C _D	
	D _i	D _o				max. min.	max. min.			
0203DP4B	2	3.5	0.750 0.730	3.25	h6	2.000	H6	3.508	2.048	
0205DP4B				2.75						1.994
0306DP4B	3	4.5		5.25		3.000		4.508		3.048
				4.75						
0404DP4B	4	5.5		4.25		4.000		5.508		4.048
0406DP4B				3.75						
0505DP4B	5	7		6.25		4.990		7.015		5.055
0510DP4B				5.75						
0606DP4B	6	8		10.25		5.990		8.015		6.055
0608DP4B				9.75						
0610DP4B	8	10		8.25		7.987		10.015		8.055
0808DP4B				7.75						
0810DP4B	10	12	10.25	9.987	12.018	10.058				
0812DP4B			9.75				9.972	12.000	9.990	
1010DP4B	12	14	12.25	11.984	14.018	12.058				
1015DP4B			11.75				11.966	14.000	11.990	
1208DP4B	12	14	15.25	11.984	14.018	12.058				
1210DP4B			14.75				11.966	14.000	11.990	
1212DP4B	12	14	10.25	11.984	14.018	12.058				
1215DP4B			9.75				11.966	14.000	11.990	

8 Standard Products

Part No.	Nominal Diameter		Wall thickness s_3	Width B	Shaft- \varnothing D_J [h6, f7, h8]	Housing- \varnothing D_H [H6, H7]	Bush- \varnothing $D_{i,a}$ ass. in H6/H7 housing	Clearance C_D							
	D_i	D_o							max. min.	max. min.	max. min.	max. min.	max. min.		
1410DP4B	14	16	1.005 0.980	10.25	f7	H7	14.058 13.990	0.092 0.006							
1415DP4B				9.75					13.984	16.018					
1420DP4B				15.25					13.966	16.000					
1515DP4B	15	17		20.25					14.984 14.966	17.018 17.000	15.058 14.990	0.092 0.006			
1525DP4B				19.75									14.75	17.000	
1615DP4B				15.25									15.984	18.018	
1625DP4B	16	18		14.75					15.984 15.966	18.018 18.000	16.058 15.990	0.092 0.006			
1820DP4B				25.25									17.984	20.021	
1825DP4B				24.75									17.966	20.000	
2015DP4B	20	23		1.505 1.475					15.25	f7	H7	20.071 19.990	0.112 0.010		
2020DP4B									14.75					19.980	23.021
2025DP4B									20.25					19.959	23.000
2030DP4B			19.75		21.980	25.021									
2215DP4B	22	25	30.25		21.980 21.959	25.021 25.000	22.071 21.990	0.112 0.010							
2220DP4B			29.75						24.980					28.021	
2225DP4B			15.25						24.959					28.000	
2515DP4B	25	28	14.75		24.980 24.959	28.021 28.000	25.071 24.990	0.112 0.010							
2525DP4B			25.25						27.980					32.025	
2830DP4B	28	32	24.75		27.959	32.000	28.085 27.990	0.126 0.010							
3020DP4B	30	34	20.25		29.980 29.959	34.025 34.000	30.085 29.990								
3030DP4B			19.75					34.975	39.025						
3040DP4B			30.25	34.950				39.000							
3520DP4B	35	39	20.25	34.975 34.950	39.025 39.000	35.085 34.990	0.135 0.015								
3530DP4B			19.75					39.975	44.025						
4030DP4B	40	44	30.25	39.975 39.950	44.025 44.000	40.085 39.990	0.135 0.015								
4050DP4B			29.75					44.975	50.025						
4530DP4B			50.25					44.950	50.000						
4550DP4B	45	50	49.75	44.975 44.950	50.025 50.000	45.105 44.990	0.155 0.015								
5040DP4B			40.25					49.975	55.030						
5060DP4B	50	55	39.75	49.975 49.950	55.030 55.000	50.110 49.990	0.160 0.015								
5540DP4B			60.25					54.970	60.030						
5540DP4B			59.75					54.940	60.000						
6040DP4B	60	65	2.505 2.460	40.25	59.970 59.940	65.030 65.000	60.110 59.990	0.170 0.020							
6050DP4B				39.75					64.970	65.110					
6060DP4B				50.25					64.940	64.990					
6070DP4B				49.75					70.030	65.110					
6070DP4B				60.25					69.970	64.990					
6570DP4B	59.75	69.940		70.000											

Part No.	Nominal Diameter		Wall thickness s_3	Width B	Shaft- \varnothing D_j [h6, f7, h8]		Housing- \varnothing D_H [H6, H7]		Bush- \varnothing $D_{i,a}$ ass. in H6/H7 housing	Clearance C_D
	D_i	D_o			max. min.	max. min.	max. min.	max. min.		
7050DP4B	70	75	2.505 2.460	50.25	f7	69.970 69.940	75.030 75.000	70.110 69.990	0.170 0.020	
7070DP4B				49.75						70.25
7580DP4B				75						80
8060DP4B	80	85	2.490 2.440	60.50	h8	80.000 79.954	85.035 85.000	80.155 80.020	0.201 0.020	
80100DP4B				59.50						100.50
85100DP4B	85	90	100.50 99.50	100.50 99.50	85.000 84.946	90.035 90.000	85.155 85.020	0.209 0.020		
9060DP4B	90	95	60.50	h7	90.000 89.946	95.035 95.000	90.155 90.020			
90100DP4B			59.50					100.50		
95100DP4B	95	100	100.50 99.50	100.50 99.50	95.000 94.946	100.035 100.000	95.155 95.020			
10060DP4B	100	105	60.50	h8	100.000 99.946	105.035 105.000	100.155 100.020	0.209 0.020		
100115DP4B			59.50						115.50	
105115DP4B	105	110	115.50 114.50	115.50 114.50	105.000 104.946	110.035 110.000	105.155 105.020			
110115DP4B	110	115	115.50 114.50	115.50 114.50	110.000 109.946	115.035 115.000	115.155 115.020			

8.6 DP4B Flanged bushes

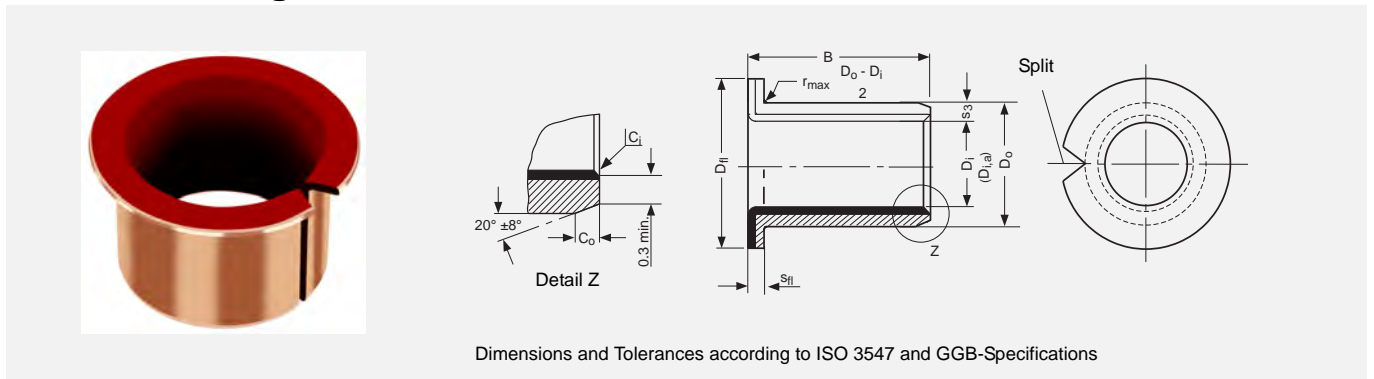

All dimensions in mm

Outside C_O and Inside C_i chamfers

Wall thickness s_3	C_O (a)		C_i (b)
	machined	rolled	
0.75	0.5 ± 0.3	0.5 ± 0.3	-0.1 to -0.4
1	0.6 ± 0.4	0.6 ± 0.4	-0.1 to -0.5
1.5	0.6 ± 0.4	0.6 ± 0.4	-0.1 to -0.7

Wall thickness s_3	C_O (a)		C_i (b)
	machined	rolled	
2	1.2 ± 0.4	1.0 ± 0.4	-0.1 to -0.7
2.5	1.8 ± 0.6	1.2 ± 0.4	-0.2 to -1.0

a = Chamfer C_O machined or rolled at the option of the manufacturer


b = C_i can be a radius or a chamfer in accordance with ISO 13715

Part No.	Nominal Diameter		Wall thickness s_3	Flange thickness s_{fl}	Flange- \varnothing D_{fl}	Width B	Shaft- \varnothing D_j [h6, f7, h8]		Housing- \varnothing D_H [H6, H7]		Bush- \varnothing $D_{i,a}$ Ass. in H6/H7 housing	Clearance C_D
	D_i	D_o					max. min.	max. min.	max. min.	max. min.		
BB0304DP4B	3	4.5	0.750	0.80	7.50	4.25	h6	3.000	H6	4.508	3.048	0.054
BB0404DP4B			0.730		6.50			2.994		4.500		
BB0505DP4B	5	7	1.005	1.05	10.50	5.25	f7	4.990	H7	7.015	5.055	0.077
			0.980		9.50			4.978		7.000		

8 Standard Products

Part No.	Nominal Diameter		Wall thickness S_3	Flange thickness S_{fl}	Flange- \varnothing D_{fl}		Width B	Shaft- \varnothing D_J [h6, f7, h8]		Housing- \varnothing D_H [H6, H7]		Bush- \varnothing $D_{1,a}$ Ass. in H6/H7 housing	Clearance C_D
	D_i	D_o			max. min.	max. min.		max. min.	max. min.	max. min.	max. min.		
BB0604DP4B	6	8	1.005 0.980	1.05 0.80	12.50 11.50	4.25	f7	5.990 5.978	H7	8.015 8.000	6.055 5.990	0.077 0.000	
BB0608DP4B						3.75							
BB0806DP4B	8	10			15.50 14.50	5.75		7.987 7.972		10.015 10.000	8.055 7.990	0.083 0.000	
BB0810DP4B						5.25							
BB1007DP4B	10	12			18.50 17.50	7.25		9.987 9.972		12.018 12.000	10.058 9.990	0.086 0.003	
BB1012DP4B						6.75							
BB1207DP4B	12	14			20.50 19.50	7.25		11.984 11.966		14.018 14.000	12.058 11.990	0.092 0.006	
BB1209DP4B						6.75							
BB1212DP4B						9.25							
BB1417DP4B	14	16			22.50 21.50	7.25		13.984 13.966		16.018 16.000	14.05 13.990	0.092 0.006	
BB1512DP4B						6.75							
BB1517DP4B	15	17			23.50 22.50	12.25		14.984 14.966		17.018 17.000	15.058 14.990	0.092 0.006	
BB1612DP4B						11.75							
BB1617DP4B	16	18			24.50 23.50	12.25		15.984 15.966		18.018 18.000	16.058 15.990	0.092 0.006	
BB1812DP4B						11.75							
BB1822DP4B	18	20			26.50 25.50	11.75		17.984 17.966		20.021 20.000	18.061 17.990	0.095 0.006	
BB2012DP4B						22.25							
BB2017DP4B	20	23			30.50 29.50	21.75		19.980 19.959		23.021 23.000	20.071 19.990	0.112 0.010	
BB2512DP4B						16.25							
BB2522DP4B	25	28			35.50 34.50	11.75		24.980 24.959		28.021 28.000	25.071 24.990	0.112 0.010	
BB3016DP4B			21.25										
BB3026DP4B	30	34	42.50 41.50	16.25	29.980 29.959	34.025 34.000	30.085 29.990	0.126 0.010					
BB3526DP4B				15.75									
BB4026DP4B	35	39	47.50 46.50	26.25	34.975 34.950	39.025 39.000	35.085 34.990	0.135 0.015					
BB4526DP4B				25.75									
BB4526DP4B	40	44	53.50 52.50	26.25	39.975 39.950	44.025 44.000	40.085 39.990	0.135 0.015					
BB4526DP4B				25.75									
BB4526DP4B	45	50	58.50 57.50	26.25	44.975 44.950	50.025 50.000	45.105 44.990	0.155 0.015					
BB4526DP4B				25.75									


8.7 DP4 Strip

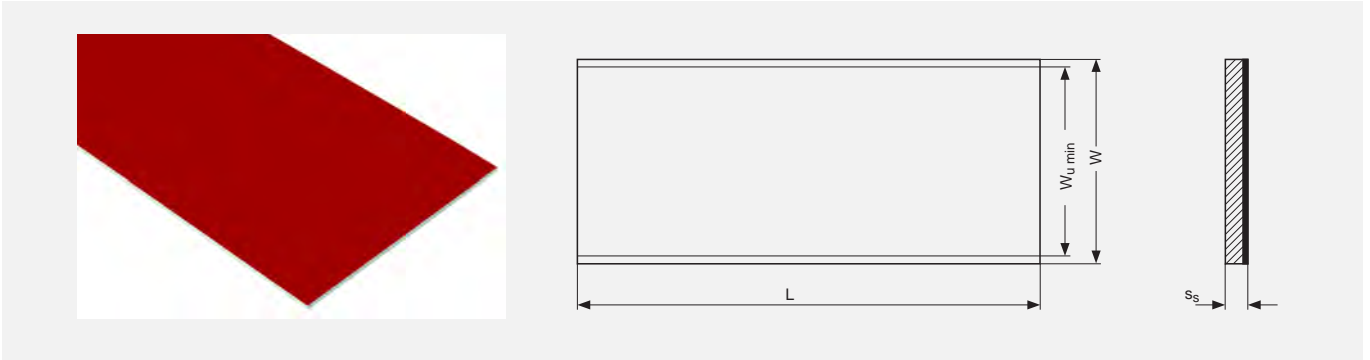

All dimensions in mm

Part No.	Length L	Total Width W	Usable Width $W_{U \min}$	Thickness s_S
	max. min.			max. min.
S07190DP4	503 500	200	190	0.74
S10190DP4				0.70
S15190DP4				1.01
S20190DP4				0.97
S25240DP4		254	240	1.52
				1.48
				1.98
				1.94
				2.46
				2.42

8.8 DP4B Strip

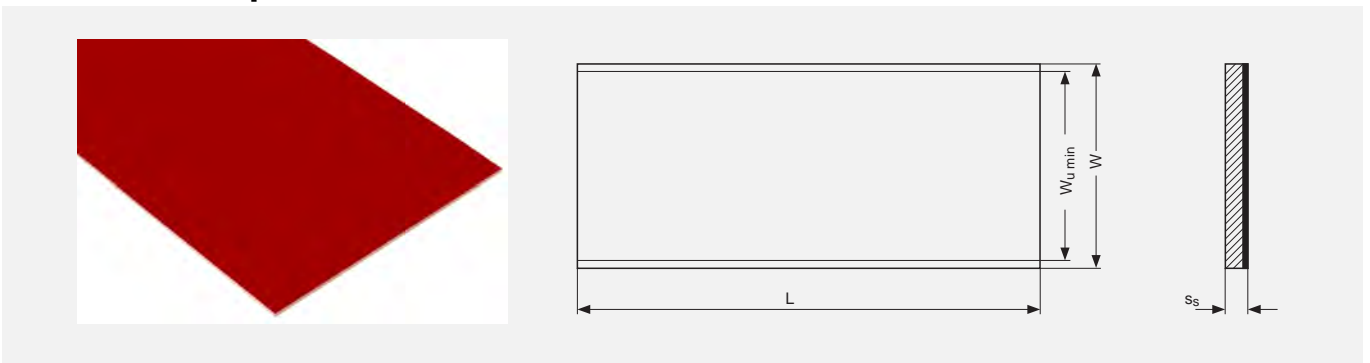

All dimensions in mm

Part No.	Length L	Total Width W	Usable Width $W_{U \min}$	Thickness s_S
	max. min.			max. min.
S07085DP4B	503 500	95	85	0.74
S10180DP4B		195	180	0.70
S15180DP4B				1.01
S20180DP4B				0.97
S25180DP4B				1.52
				1.48
				1.98
				1.94
				2.46
				2.42

9 Test Methods

9.1 Measurement of Wrapped Bushes

It is not possible to accurately measure the external and internal diameters of a wrapped bush in the free condition. In its free state a wrapped bush will not be perfectly cylindrical and the butt joint may be open. When correctly installed in a housing the butt joint will be tightly closed and the bush will

conform to the housing. For this reason the external diameter and internal diameter of a wrapped bush can only be checked with special gauges and test equipment.

The checking methods are defined in ISO 3547 Part 1 to 7.

Test A of ISO 3547 Part 2

Checking the external diameter in a test machine with checking blocks and adjusting mandrel.

Test A of ISO 3547 Part 2 on 2015DP4	
Checking block and setting mandrel $d_{ch,1}$	23.062 mm
Test force F_{ch}	4500 N
Limits for Δz	0 and -0.065 mm
Bush Outside diameter D_o	23.035 to 23.075 mm

Table 18: Test A of ISO 3547 Part 2

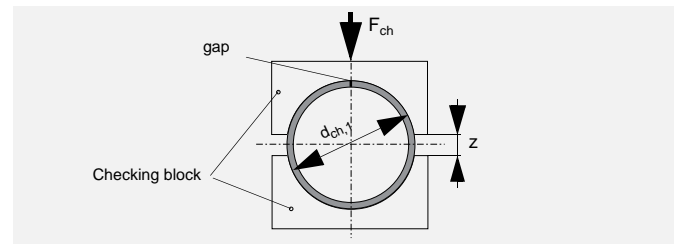


Fig. 40: Test A, Data for drawing

Test B (alternatively to Test A)

Check external diameter with GO and NO GO ring gauges.

Test C

Checking the internal diameter of a bush pressed into a ring gauge, which nominal diameter corresponds to the dimension specified in table 6 of ISO 3547 Part 1.

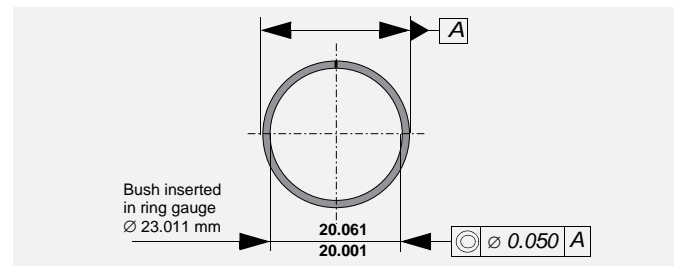


Fig. 41: Test C, Data for drawing (example $D_i = 20$ mm)

Measurement of Wall Thickness (alternatively to Test C)

The wall thickness is measured at one, two or three positions axially according to the bearing dimensions.

B [mm]	X [mm]	Measurement position
≤ 15	B/2	1
$>15 \leq 50$	4	2
$>50 \leq 90$	6 and B/2	3
>90	8 and B/2	3

Table 19: Measurement position for wall thickness

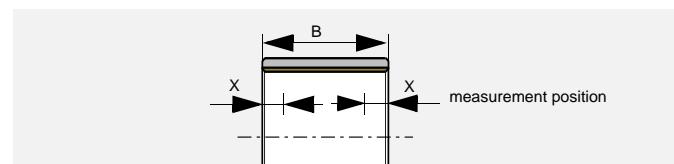


Fig. 42: Wall thickness measurement position

Test D

Check external diameter by precision measuring tape.

10 Data Sheet for bearing design

Company:

Project:

Application:

Date:

Existing Design New Design
 Quantity Annual


Contact name:

Tel.:

Fax:

Email:

Drawing attached YES NO

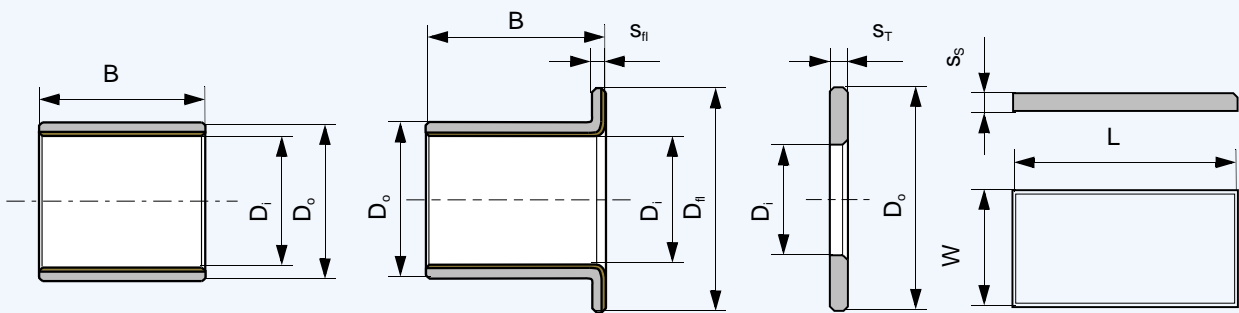

Cylindrical Bush
 Flanged Bush
 Thrust Washer
 Slideplate
 Special (Sketch)

Steady load
 Rotating load
 Rotational movement
 Oscillating movement
 Linear movement

Dimensions in mm

Inside Diameter	D_i	<input type="text"/>
Outside Diameter	D_o	<input type="text"/>
Length	B	<input type="text"/>
Flange Diameter	D_{fi}	<input type="text"/>
Flange Thickness	s_{fi}	<input type="text"/>
Length of slideplate	L	<input type="text"/>
Width of slideplate	W	<input type="text"/>
Thickness of slideplate	s_s	<input type="text"/>

Load

Radial load	F [N]	<input type="text"/>
Axial load	F [N]	<input type="text"/>

Movement

Rotational speed	n [1/min]	<input type="text"/>
Speed	v [m/s]	<input type="text"/>
Length of Stroke	L_s [mm]	<input type="text"/>
Frequency of Stroke	[1/min]	<input type="text"/>
Angular displacement	ϕ [°]	<input type="text"/>
Oscillating frequency	n_{osc} [1/min]	<input type="text"/>

Service hours per day

Continuous operation	[h]	<input type="text"/>
Intermittent operation	[h]	<input type="text"/>

Fits and Tolerances

Housing (\emptyset , tolerance)	D_H	<input type="text"/>
Shaft (\emptyset , tolerance)	D_J	<input type="text"/>

Mating surface

Material	<input type="text"/>
Hardness	HB/HRC <input type="text"/>
Surface roughness	R_a [μm] <input type="text"/>

Operating Environment

Temperature - ambient	T_{amb}	<input type="text"/>
Temperature - min/max	T_{min}/T_{max}	<input type="text"/>

Housing material

Assembly with good heat transfer properties
 Assembly with poor heat transfer properties

Dry operation With lubricant

If grease, type with technical datasheet
 If oil, type with technical datasheet

- Oil splash
 - Oil bath
 - Oil circulation

Service life

Required service life L_H [h]

10 Data Sheet for bearing design

Formula Symbols and Designations

Formula Symbol	Unit	Designation
A	mm ²	Surface area of DP4 bearing
A _M	mm ²	Surface area of mating surface in contact with DP4 bearing (slideway)
a _B	-	Bearing size factor
a _C	-	Application factor for bore burnishing
a _E	-	High load factor
a _{E1}	-	Specific load factor (slideways)
a _{E2}	-	Speed, temperature and material factor (slideways)
a _{E3}	-	Relative contact area factor (slideways)
a _L	-	Life correction constant
a _M	-	Mating surface material factor
a _T	-	Temperature application factor
B	mm	Nominal bush width
C	1/min	Dynamic load frequency
C _D	mm	Installed diametral clearance
C _I	mm	Inside chamfer
C _O	mm	Outside chamfer
C _T	-	Total number of dynamic load cycles
D _C	mm	Diameter of burnishing tool
D _{fl}	mm	Nominal bush flange OD
D _H	mm	Housing diameter
D _I	mm	Nominal bush and thrust washer ID
D _{I,a}	mm	Bush ID when assembled in housing
D _J	mm	Shaft diameter
D _{Nth}	nvt	Max. thermal neutron dose
D _O	mm	Nominal bush and thrust washer OD
D _γ	Gy	Max. Gamma radiation dose G _γ = J/kg
d _D	mm	Dowel hole diameter
d _L	mm	Oil hole diameter
d _P	mm	Pitch circle diameter for dowel hole
F	N	Bearing load
F _{ch}	N	Test load
F _i	N	Insertion force
f	-	Coefficient of friction

Formula Symbol	Unit	Designation
H _a	mm	Depth of housing recess (e.g. for thrust washers)
H _d	mm	Diameter of housing recess (thrust washers)
L	mm	Strip length
L _H	h	Bearing service life
L _S	mm	Length of stroke (slideway)
n	1/min	Rotational speed
n _E	1/min	Equivalent rotational speed for oscillating movement
n _{osc}	1/min	Oscillating movement frequency
p	MPa	Specific load
p _{lim}	MPa	Specific load limit
p _{sta,max}	MPa	Maximum static load
p _{dyn,max}	MPa	Maximum dynamic load
Q	-	Number of load/movement cycles
R _a	μm	Surface roughness (DIN 4768, ISO/DIN 4287/1)
R _{OB}	Ω	Electrical resistance
s ₃	mm	Bush wall thickness
s _{fl}	mm	Flange thickness
s _S	mm	Strip thickness
s _T	mm	Thrust washer thickness
T	°C	Temperature
T _{amb}	°C	Ambient temperature
T _{max}	°C	Maximum temperature
T _{min}	°C	Minimum temperature
v	m/s	Sliding speed
W	mm	Strip width
W _{u min}	mm	Minimum usable strip width
Z _T	-	Total number of cycles
α ₁	10 ⁻⁶ /K	Coefficient of linear thermal expansion parallel to surface
α ₂	10 ⁻⁶ /K	Coefficient of linear thermal expansion normal to surface
σ _c	MPa	Compressive yield strength
λ	W/mK	Thermal conductivity
φ	°	Angular displacement
η	cP	Dynamic viscosity

Product Information

GGB gives an assurance that the products described in this document have no manufacturing errors or material deficiencies.

The details set out in this document are registered to assist in assessing the material's suitability for the intended use. They have been developed from our own investigations as well as from generally accessible publications. They do not represent any assurance for the properties themselves.

Unless expressly declared in writing, GGB gives no warranty that the products described are suited to any particular purpose or specific operating circumstances. GGB accepts no liability for any losses, damages or costs however they may arise through direct or indirect use of these products.

GGB's sales and delivery terms and conditions, included as an integral part of quotations, stock and price lists, apply absolutely to all business conducted by GGB. Copies can be made available on request.

Products are subject to continual development. GGB retains the right to make specification amendments or improvements to the technical data without prior announcement.

Edition 2012 (This edition replaces earlier editions which hereby lose their validity).

Declaration on lead contents of GGB products/compliance with EU law

Since July 1, 2006 it has been prohibited under Directive 2011/65/EU (restriction of the use of certain hazardous substances in electrical and electronic equipment; ROHS Directive) to put products on the market that contain lead, mercury, cadmium, hexavalent chromium, polybrominated biphenyls (PBB) or polybrominated diphenyl ethers (PBDE). Certain applications listed in the annex to the ROHS Directive are exempted. A maximum concentration value of 0.01% by weight and per homogeneous material, for cadmium and of 0.1% by weight and per homogeneous material, for lead, mercury, hexavalent chromium, PBB and PBDE shall be tolerated.

According to Directive 2011/65/EU on end-of life vehicles, since July 1, 2003 it has been prohibited to put on the market materials and components that contain lead, mercury, cadmium or hexavalent chromium. Due to an exceptional provision, lead-containing bearing shells and bushes could still be put on the market up until July 1, 2008. This general exception expired on July 1, 2008. A maximum concentration value of up to 0.1% by weight and per homogeneous material, for lead, hexavalent chromium and mercury shall be tolerated.

All products of GGB, with the exception of DU®, DU-B™, DB™, PICAL2™, SY™, SP™, GGB-CSM™115, GGB-CSM™118, GGB-CSM™124, GGB-CSM™125, GGB-CBM™311, GGB-CBM™312, GGB-CBM™322, GGB-CBM™341 and GGB-CBM™342 satisfy these requirements of 2011/65/EU from 08.06.2011 (ROHS Directive).

All products manufactured by GGB are also compliant with REACH Regulation (EC) No. 1 907/2006 of December 18, 2006.

Health Hazard - Warning

Fabrication

At temperatures up to 250 °C the polytetrafluoroethylene (PTFE) present in the lining material is completely inert so that even on the rare occasions in which DP4 bushes are drilled, or sized, after assembly there is no danger in boring or burnishing.

At higher temperatures however, small quantities of toxic fumes can be produced and the direct inhalation of these can cause an influenza type of illness which may not appear for some hours but which subsides without after-effects in 24-48 hours.

Such fumes can arise from PTFE particles picked up on the end of a cigarette. Therefore smoking should be prohibited where DP4 is being machined.

DP4™, DP4B™, DX®, DX®10 with DuraStrong™ technology, DS™ and HX™ are trademarks of GGB.

Visit us on the internet:
www.ggbearings.com

